

**DESIGN, CONSTRUCTION AND TESTING OF AN IMPROVED CASTING
POURING LADLE**

BY

EMMANUEL STEPHEN

**DEPARTMENT OF MECHANICAL ENGINEERING
AHMADU BELLO UNIVERSITY,
ZARIA, NIGERIA**

DECEMBER, 2017

**DESIGN, CONSTRUCTION AND TESTING OF AN IMPROVED CASTING
POURING LADLE**

BY

**Emmanuel STEPHEN, B. ENG., (A.B.U.), 2011
P13EGME8053**

**A THESIS SUBMITTED TO THE SCHOOL OF POSTGRADUATE STUDIES,
AHMADU BELLO UNIVERSITY, ZARIA**

**IN PARTIAL FULFILLMENT OF THE REQUIREMENTS FOR THE AWARD
OF MASTER DEGREE IN MECHANICAL ENGINEERING**

**DEPARTMENT OF MECHANICAL ENGINEERING,
FACULTY OF ENGINEERING
AHMADU BELLO UNIVERSITY,
ZARIA, NIGERIA**

DECEMBER, 2017

DECLARATION

I declare that the work in this dissertation entitled “**Design, Construction and Testing of an Improved Casting Pouring Ladle**” has been carried out by me in the Department of Mechanical Engineering. The information derived from the literature has been duly acknowledged in the text and a list of references provided. No part of this thesis was previously presented for another degree or diploma at this or any other Institution.

Emmanuel Stephen _____

Name of Student

Signature

Date

DEDICATION

I dedicate this research dissertation to my late brother Late Ijai G. Stephen and to my family (the family of Mr and Mrs. Stephen P.M. Gadzama).

ACKNOWLEDGEMENTS

I give glory and thanks unto God Almighty for the gift of life, privilege and opportunity to complete my studies from Nursery school up to this Postgraduate level.

My profound gratitude goes to my supervisors; Engr. Prof.S.A. Yaro and Engr. Prof.M. Dauda for given me their time, interest, useful suggestions, and constructive criticism. Indeed, they have been the pillars to the success of this dissertation. Also, my appreciation goes to Mr H.Elisha, Mr M.Ebiloma, Mr.J. Dogara, Mr A.Mbaratan, Mr O. Danjuma, Mr M. Dalis, Engr. Prof. D.S. Yawas, Engr.Dr. D.M. Kulla, Engr. Dr. U.Samaila, Engr. K. Laminu etc for their contributions towards the success of this thesis.

Equally, my gratitude goes to the entire staff of the Department of Mechanical Engineering, Ahmadu Bello University, Zaria-Nigeria, especially my lecturers, the Technologists and the Non-academic staff. Also, my appreciation goes to my colleagues for their suggestions and contributions.

I shall forever be grateful to my Head of Department/Coordinator NADDC Zaria Office, Engr. Dr. F.M. Achiv, HOD T&S/ Head Training Committee NADDC Zaria Office, Engr. Dr. L.S. Isah, Engr. Dr. N. Omisanya, Engr. A.N. Ayinde, Engr. O.A. Oyetade, Mr A.T. Ezekiel, Mr Y.O. Shoyoye, Mr S. Adamu, Mr S.O. Babarinsa, Mr M.A. Suleiman, Mr O.O. Jolaiya, Mr A. Bawa, Mr. J. Maimolo, Mr S. Ambi, Mal Suleiman, Mr S. Bashir, Mr I. Ishola, Mrs. I. Rejina, Miss. A.C. Juliet, Mr T.T. KyumNom and all the staff of National Automotive Design and Development Council.

I am grateful to God Almighty for the life of my family, my parent, Mr and Mrs Stephen P.M. Gadzama for their immense contributions, support, love and prayer towards my success. Also to my brothers Mr. Sunday, Mr. Bulus, Mr. Luka, Mr Ijulu and my sister Miss. Kellu Stephen Gadzama. You are all wonderful and supportive. You are part of my success in life. My gratitude goes to Rev. A.M. Gadzama for his concern and contribution to the success of my research, the Prayer Unit of EYN Church and the entire members of the church for contributing to my success in life.

I want to appreciate Mr Zamani and Mr Danladi of the Dept. of Metallurgical and Material Engineering A.B.U. Zaria, Mal Mu'azu and Mal Aminu of the Dept. of Mechanical Engineering A.B.U. Zaria, Dr. Mumah and Dr. Hassan of Centre for Solid Mineral Research and Development Kaduna Polytechnic. To as many that contributed in one way or the other towards the success of this thesis whose names are not mentioned, am saying a big thank you. May God Almighty richly reward you all.

ABSTRACT

A ladle is a foundry tool or equipment specially designed to pour molten metal into a prepared mould. The pouring rate or consistency is one of the factors that may lead to a defect in a cast. To avoid casting defects (cold shut and misrun) associated with pouring, there is need for the design of a suitable pouring ladle that will reduce the time to be spent in crucible lifting, to pouring the molten metal from the crucible to fill the mould at consistent rate. In this research, a pouring ladle machine of 50 kg molten Aluminium alloy was successfully designed, constructed and tested. The result of this research showed that the total time spent in lifting the crucible containing molten Aluminium alloy from the furnace to filling the mould using the pouring ladle was 53.48 sec while when using the hand-shank ladle was 81.80 sec. The speed of pouring when using the pouring ladle machine and hand-shank ladle were 0.42cm/s, 0.43cm/s respectively. The micrograph of both samples show visible well defined coarse grains. This could be due to the even distribution of the constituents as cooling takes place since no too much time was taken to pour the liquid metal into the mould. The result of the XRF tests shows the presence of the various elements detected in the alloy with their percentages at different energy level with the high percentage of Silicon detected. The designed ladle machine was able to give casts with no cold shut and misruns cast defects with less time spent and fatigue during pouring. There was time difference of 28.32 sec (34.62 % time saving) and speed difference of 0.01 cm/s (2.33 % speed increase).

TABLE OF CONTENTS

	Page
Title Page - - - - -	ii
Declaration - - - - -	iii
Certification - - - - -	iv
Dedication - - - - -	v
Acknowledgements - - - - -	vi
Abstract - - - - -	vii
Table of Contents - - - - -	viii
List of Figures - - - - -	xii
List of Plates - - - - -	xiii
List of Tables - - - - -	xv
List of Appendices - - - - -	xvi

CHAPTER ONE: INTRODUCTION

1.1 Background of the Study - - - - -	1
1.2 Statement of the Problem - - - - -	1
1.3 The Present Work - - - - -	2
1.4 Aim and Objectives - - - - -	2
1.5 Significance of the Research - - - - -	3
1.6 Justification of the Research - - - - -	3
1.7 Scope and Limitations of the Research - - - - -	4

CHAPTER TWO: LITERATURE REVIEW

2.1 Founding or Casting - - - - -	5
2.2 Advantages of Casting Process - - - - -	5
2.3 Description of Ladle - - - - -	6
2.4Ladle and their Types - - - - -	7

2.4.1 Hand casting ladle	-	-	-	-	-	-	-	7
2.4.2 Hand-shank Casting Ladle	-	-	-	-	-	-	-	7
2.4.3 Transfer Ladle	-	-	-	-	-	-	-	7
2.4.4 Treatment Ladle	-	-	-	-	-	-	-	8
2.5 Ladle Pour Design-	-	-	-	-	-	-	-	9
2.5.1 Lip Pour design	-	-	-	-	-	-	-	9
2.5.2 Teapot Spout design	-	-	-	-	-	-	-	9
2.5.3 Lip-axis Design	-	-	-	-	-	-	-	9
2.5.4 Bottom Pour Design	-	-	-	-	-	-	-	9
2.6 Review of Related Past Works	-	-	-	-	-	-	-	10
2.7 Knowledge Gap	-	-	-	-	-	-	-	11

CHAPTER THREE: MATERIALS AND METHODS

3.1 Description of the Pouring Ladle Machine	-	-	-	-	-	-	-	12
3.2 Design Consideration	-	-	-	-	-	-	-	14
3.3 Design Theory and Procedure of the Pouring Ladle and its Components								15
3.3.1 Design of the tong gripping system	-	-	-	-	-	-	-	15
3.3.2 Design of the lifting/lowering mechanism	-	-	-	-	-	-	-	16
3.3.3 Design of the tilting mechanism	-	-	-	-	-	-	-	18
3.3.4 Design of the railing mechanism	-	-	-	-	-	-	-	19
3.3.5 Design of the machine frame	-	-	-	-	-	-	-	20
3.3.6 Factor of safety	-	-	-	-	-	-	-	21
3.4 Results of Design Calculation	-	-	-	-	-	-	-	22
3.4.1 Tong gripping System	-	-	-	-	-	-	-	22
3.4.2 Lifting/lowering Mechanism	-	-	-	-	-	-	-	22
3.4.3 Tilting Mechanism	-	-	-	-	-	-	-	24

3.4.4 Railing Mechanism	-	-	-	-	-	-	-	25
3.4.5 Machine Frame	-	-	-	-	-	-	-	26
3.4.6 Factor of Safety	-	-	-	-	-	-	-	26
3.5 Selection of Materials for the Fabrication and Assembly of the Pouring Ladle								26
3.5.1 Tong Gripping System	-	-	-	-	-	-	-	27
3.5.2 Lifting/lowering Mechanism	-	-	-	-	-	-	-	27
3.5.3 Tilting Mechanism	-	-	-	-	-	-	-	28
3.5.4 Railing Mechanism	-	-	-	-	-	-	-	28
3.5.5 Machine Frame	-	-	-	-	-	-	-	28
3.6 Fabrication and Assembly of the Pouring Ladle	-	-	-	-	-	-	-	28
3.6.1 Fabrication Process Plan of the Ladle Components	-	-	-	-	-	-	-	28
3.6.2 Assembly of the Ladle Component Parts	-	-	-	-	-	-	-	33
3.6.3 Principle of Operation of the Ladle	-	-	-	-	-	-	-	33
3.6.4 Cost Analysis of the Pouring Ladle	-	-	-	-	-	-	-	34
3.7 Performance Evaluation/Testing of the Pouring Ladle Machine	-	-	-	-	-	-	-	36
3.7.1 Performance Evaluation using Water and Aluminium Alloy Molten Metal								36
3.7.2 Determination of the Speed of Pouring	-	-	-	-	-	-	-	38
3.7.3 Non-destructive Test	-	-	-	-	-	-	-	38

CHAPTER FOUR: RESULTS AND DISCUSSION

4.1 Results	-	-	-	-	-	-	-	40
4.1.1 Result of the Pouring Ladle Machine	-	-	-	-	-	-	-	40
4.1.2 Determination of the Speed of Pouring	-	-	-	-	-	-	-	41
4.1.3 Non-destructive Test	-	-	-	-	-	-	-	42
4.2 Discussion of Results	-	-	-	-	-	-	-	47
4.2.1 Result of Performance Evaluation of the Pouring Ladle	-	-	-	-	-	-	-	47

4.2.2 Non-destructive Test	-	-	-	-	-	-	-	-	49
----------------------------	---	---	---	---	---	---	---	---	----

CHAPTER FIVE: CONCLUSION AND RECOMMENDATIONS

5.1 Conclusion	-	-	-	-	-	-	-	-	51
----------------	---	---	---	---	---	---	---	---	----

5.2 Recommendation	-	-	-	-	-	-	-	-	52
--------------------	---	---	---	---	---	---	---	---	----

5.3 Contribution to Knowledge	-	-	-	-	-	-	-	-	52
-------------------------------	---	---	---	---	---	---	---	---	----

REFERENCES	-	-	-	-	-	-	-	-	54
------------	---	---	---	---	---	---	---	---	----

APPENDICES	-	-	-	-	-	-	-	-	56
------------	---	---	---	---	---	---	---	---	----

LIST OF FIGURES

Figures	Page
Figure 2.1: Hand-shank casting ladle - - - - -	7
Figure 3.1: Sketch (Orthographic views) of the casting pouring ladle machine	13
Figure 3.2: Schematic diagram of the shaft - - - - -	16
Figure 3.3: Schematic diagram of shafts - - - - -	17
Figure 3.4: Schematic diagram of crank lever arm - - - - -	18
Figure 3.5: Schematic diagram of I-beam - - - - -	19
Figure 3.6: Schematic diagram of the plate - - - - -	20
Figure 3.7: Schematic diagram of standing frame - - - - -	21
Figure 4.1: Average pouring time for the ladle machine and hand-shank ladle using water - - - - -	48
Figure 4.2: Average pouring time for ladle machine and hand-shank ladle using Aluminium alloy molten metal - - - - -	49

LIST OF PLATES

Plates	Page
Plate 2.1: Transfer ladle - - - - -	8
Plate 2.2: Treatment ladle - - - - -	8
Plate 3.1: Pattern used for the production of mould for the casting - -	37
Plate 3.2a: Sand mould for pouring ladle - - - - -	37
Plate 3.2b: Sand mould for hand-shank ladle - - - - -	37
Plate 3.3: Cast sample of improved casting pouring ladle - - -	38
Plate 3.4: Cast sample of hand-shank ladle - - - - -	38
Plate 3.5: Samples for metallography test. Where sample A was from pouring ladle and sample B from hand-shank ladle - - - -	39
Plate 3.6: Using the metallurgical microscope model NJF-1 for snap capturing of the samples - - - - -	39
Plate 3.7: Samples for metallography test. Where sample A was from pouring ladle and sample B from hand-shank ladle - - - -	39
Plate 3.8: Using the XRF machine model XL3t 950 for snap capturing of the samples - - - - -	39
Plate 4.1: Cope side of the water jacket cast using ladle machine -	42
Plate 4.2: Drag side of the water jacket cast using ladle machine -	42
Plate 4.3: Front side of the crank lever cast using ladle machine -	43
Plate 4.4: Rear side of the crank lever cast using ladle machine -	43
Plate 4.5: Cope side of the bearing cap cast using ladle machine -	43
Plate 4.6: Drag side of the bearing cap cast using ladle machine -	43
Plate 4.7: Cope side of the water jacket cast using manual hand-shank ladle	43
Plate 4.8: Drag side of the water jacket cast using manual hand-shank ladle	43

Plate 4.9: Front side of the crank lever cast using manual hand-shank ladle	44
Plate 4.10: Rear side of the crank lever cast using manual hand-shank ladle	44
Plate 4.11: Cope side of the bearing cap cast using manual hand-shank ladle	44
Plate 4.12: Drag side of the bearing cap cast using manual hand-shank ladle	44
Plate 4.13a: Micrograph test for sample using pouring ladle machine (X100)	45
Plate 4.13b: Micrograph test for sample using hand-shank ladle (X100)	45
Plate 4.14: Spectra for cast sample from machine ladle at different energy levels	46
Plate 4.15: Spectra for cast sample from hand-shank ladle at different energy levels	47

LIST OF TABLES

Tables	Page
Table 3.1: Design calculations for the components of the ladle machine -	22
Table 3.2: Material Components for tong gripping system - - -	27
Table 3.3: Material Componentsfor lifting/lowering mechanism - -	27
Table 3.4: Material Componentsfor tilting mechanism - - -	28
Table 3.5: Material Componentsfor railing mechanism - - -	28
Table 3.6: Material Components for machine frame - - - -	28
Table 3.7: Fabrication process plan of the pouring ladle and the tools/machines used - - - - - - - - -	30
Table 3.8: Bill of Materials for the pouring ladle machine - - -	34
Table 3.9: Labour and cost of production of the pouring ladle machine -	36
Table 4.1: Result of Pouring Time for Ladle Machineusing water - -	40
Table 4.2: Result of Pouring Time for Hand-shank Ladle using Water -	40
Table 4.3: Result of Pouring Timefor Ladle Casting Machine using Aluminnium Alloy - - - - - - - - -	41
Table 4.4: Result of Pouring Time for Hand-shank Ladle usingAluminium Alloy	41

LIST OF APPENDICES

Appendices	Pages
Appendix A (Drawings of the machine and machine components) - -	56
Appendix B (Fabrication Process and Performance Evaluation of the Ladle Machine) - - - - -	57
Appendix C (Result of XRF Test from Centre for Minerals Research and Development, Kaduna Polytechnic) - - - - -	58

CHAPTER ONE

INTRODUCTION

1.1 Background of the Study

Metal casting is one of the most widely used techniques for the production of metal parts. It is the process of forming metallic objects by melting metal, pouring it into a shaped cavity called a mould and allowing it to solidify. Heat is absorbed by and transferred through the mould wall during pouring of molten metal in mould cavity (Choudhari *et al.*, 2014).

Pouring of molten metal into a prepared mould is one of the processes involved in the casting process in a foundry. The ladle is the foundry tool or equipment specially designed to pour the molten metal into a prepared mould. This makes the ladle to play a very significant role in the casting process. The pouring process can affect the quality of the casting or cause defect to the cast or fatigue or even injury to the foundry men due the Manual Material Handling (MMH). Some of the factors that can lead to casting defects (such as misruns and cold shut) include; the ladle design or the type of ladle used, the pouring rate or consistency, the shaking or vibration by the foundry men when tilting the casting ladle for pouring process due to tiredness and fatigue and the delay in lifting the crucible from the furnace to pouring of the molten metal into the prepared mould (Konz, 1995).

1.2 Statement of the Problem

It is usually desired that a cast product should not have any defect. But defects occur which may be as a result of the many activities that are involved during casting process. The pouring rate or consistency is one of these factors that may lead to a defect in a cast. In order to avoid a defect which may be as a result of pouring of the molten metal from the crucible (casting defect such as cold shut and misrun), there is need for the design of a suitable ladle that will reduce the time to be spent in crucible lifting, to pouring the molten metal from the crucible into the mould at consistent rate.

Manual Material Handling (MMH) is one of the major causes of severe industrial injury (Ciriello, 2005; Dempsey and Hashemi, 1999). It has been estimated that more than a quarter of all injuries related to industrial work are directly associated with MMH activities (Konz, 1995).

Also, fatigue resulting from lifting of the ladle by two or more operators and bending to tilt it to pour the molten metal from the crucible into the mould affect the pouring rate or consistency. To solve these problems, the ladle was designed to assist the operators to lift and lower the crucible and tilt the fork lift for pouring Aluminium alloy molten metal from the crucible into the prepared mould using crank lever mechanism.

1.3 The Present Work

The research work was focused on the design, construction and testing of an improved casting pouring ladle which would be used to lift a crucible containing 50kg molten Aluminium alloy metal from a crucible furnace and poured it into a prepared mould at a relatively consistent pouring rate with less fatigue on the operators while pouring the molten metal. The time taken for the pouring and speed of pouring from both the ladle machine and manual hand-shank ladle were computed and compared.

1.4 Aim and Objectives

The aim of this research is to design, construct and test an improved casting pouring ladle that could be used in a foundry workshop to cast 50 kg liquid Aluminium alloy.

The specific objectives are:

- i. To carry out the design analysis of the improved casting pouring ladle.
- ii. To construct the various component parts of the pouring ladle and assemble them.
- iii. To carry out performance evaluation in determining the pouring time and speed of the ladle.

- iv. To carry out non-destructive test on the Aluminium alloy casts.

1.5 Significance of the Research

To solve the problems associated with pouring process such as misrun and cold shut, the ladle was designed to assist the operators to lift and lower the crucible and tilt the fork lift for pouring the molten metal from the crucible into the prepared mould using crank lever mechanism.

The cost to be incurred in designing a mechanically automated ladle would be reduced to minimum because in this research work, there would be no need for electricity or electric motor, pneumatic or hydraulic system.

The operators involved in the pouring process are reduced to one (1) when using this machine because only one operator would be required to operate the machine instead of two or more operators as in the case of using the manual hand-shank ladle for the pouring process.

1.6 Justification of the Research

This research was carried out to design, construct and test an improved casting pouring ladle for Aluminium alloy that would reduce the time delay in lifting and pouring process of casting from a crucible into a mould with less stress and fatigue as in the case of manual hand-shank ladle.

There is need for the pouring to be relatively consistent, because inconsistent pouring may cause turbulence or sudden solidification of the molten metal in the gate. Also, when too much time is spent in between lifting of crucible from the furnace to pouring, the molten metal may start to solidify inside the crucible or when it is poured into the mould. These can cause cold shut or misrun.

Krzystof *et al.* (2013), stated that one of the most important faults occurring during casting is a misrun, which may be caused both by pouring temperature being too low and insufficient castability of the liquid metal.

The posture and heat from the crucible and molten metal induces stress to the operators when using the hand shank ladle for pouring process. This stress makes the operators' hands to be shaking while pouring. This makes the pouring not to be consistent, thereby causing a casting defect such as cold shut or misrun.

1.7 Scope and Limitations of the Research

The scope and limitations of this research are:

1. To design and construct a casting ladle of 50 kg charge capacity of molten Aluminium alloy metal for use in sand casting only where the metal is melted in crucible pit furnace.
2. There would be no use of electric motor or hydraulic cranes in design and construction of the improved casting pouring ladle.
3. Only one direction of pouring and so the moulds should be arranged linearly with their sprue basin placed close to the ladle machine.

CHAPTER TWO

LITERATURE REVIEW

2.1 Founding or Casting

Founding or casting produces casts that are close to the final product shape, i.e., “near-net shape” components. Castings are produced by pouring molten metal into moulds, with cores used to create hollow internal sections. After the metal has cooled sufficiently, the casting is separated from the mould and undergoes cleaning and finishing techniques as appropriate.

According to Richard *et al.* (1967), founding or casting may be defined as a metal object obtained by allowing molten metal to solidify in a mould. The shape of the object is being determined by the shape of the mould cavity. Founding or casting is the process of forming metal objects by melting metal and pouring it into moulds. A foundry is a commercial establishment for founding. Practically all metal is initially cast.

According to Baker (1997), Foundry Engineering is one of the earliest methods of manufacturing of products. The history of precision foundry began around 5000 years ago, together with the beginning of the demand for shaped metal products, tools and weapons.

Kalpakjian, (1995) stated that metal casting has always been one of the most important and widely used manufacturing processes. Egyptians used solidification processing to create near net-shaped components 5100 years ago.

2.2 Advantages of Casting Process

Certain advantages are inherent in the metal casting process. These may form the basis for choosing casting as a process to be preferred over other metal shaping process in a particular case. Some of the main advantages of the casting process can be given as follows:

1. Most intricate shapes both internal and external may be cast.
2. Because of their nature, some metals can only be cast since they cannot be shaped by other methods

3. Construction may be simplified. A number of separate items in an assembly can sometimes be integrated to be cast as a single piece.
4. Highly adaptable to mass production.
5. Extremely large, heavy metal objects may be cast that would be difficult and/or economically impossible to produce otherwise.
6. Some engineering properties are obtained more favourably in cast metals: in general, a wide range of alloy compositions and properties is produced in cast form, and the properties available are generally isotropic.
7. Generally, casting cost low when compared with the other metal forming processes(Derya, 2005).

2.3 Description of Ladle

Ladles in the steel plant environment are used with refractory linings to hold the molten metal for casting, temperature control, deoxidation, addition of alloys and inclusion floatation. Ladles are designed to be heat resistant and strong. Moreover, it is also necessary that a ladle be heat insulated. Proper heat insulation is required so that the molten steel contained in the ladle remains at a proper temperature. The ladle is consisting of ladle housing; thermal insulation, lifting sling and mechanical gear mechanism. The ladle structure is multi-layered because of the fact that a ladle should be strong and heat insulated. The inner face of the ladle is built from specialized refractory bricks. These bricks are resistant to high temperature, thus making it possible for the ladle to hold molten steel. Two types of bricks are used to construct the inner surface. One type of brick is used to construct part of the surface that will interact with the liquid steel while the other type of brick is used to construct the surface that will interact with the slag layer above the molten metal (Niraj, 2013).

2.4 Ladle and their Types

The basic ladle design includes many variations that improve the usage of the ladle for specific tasks. Ladles can be classified depending upon applications (Niraj, 2013).

2.4.1 Hand casting ladle

The hand ladle is a small ladle which can be handled by a single individual/operator. It is usually used to carry small crucibles for the pouring operation.

2.4.2 Hand-shank (or Bull Ladle) casting ladle

A ladle used to pour molten metal into mould(s) to produce the casting. This type of ladle requires two operators to handle it. The crucible to be carried is usually larger than that to be carried using the hand ladle. (Niraj, 2013). See Figure 2.1.



Figure 2.1: Hand-shank casting ladle (Niraj, 2013)

2.4.3 Transfer Ladle

A ladle used to transfer molten metal from a primary melting furnace to either a holding furnace or an auto-pour unit. For the transportation of very large volumes of molten metal, such as in steel mills, the ladle can run on wheels, a purpose-built ladle transfer car or be slung from an overhead crane and will be tilted using a second overhead lifting device (Niraj, 2013). See Plate 2.1.



Plate2.1:Transfer ladle (Niraj, 2013)

2.4.4TreatmentLadle

A ladle used for a process to take place within the ladle i.e. to change some aspect of the molten metal. A typical example is the conversion of cast iron to ductile iron by the addition of various elements into the ladle (Niraj, 2013).Ladles are often designed for special purposes such as adding [alloys](#) to the molten metal. Ladles may also have porous plugs inserted into the base, so inert gases can be bubbled through the ladle to enhance alloying or metallic treatment practices. See Plate2.2.



Plate 2.2:Treatment ladle (Niraj, 2013)

2.5 Ladle Pour Design

Ladles pour design can be:

2.5.1 Lip Pour Design

For lip pour design, the ladle is tilted and the molten metal pours out of the ladle like water from a [pitcher](#). The molten metal flows or pours from the top of the ladle (Sharma, 2001).

2.5.2 Teapot Spout Design

The teapot spout design, like a teapot, takes liquid from the base of the ladle and pours it out through a lip-pour spout. Any impurities in the molten metal will form on the top of the metal so by taking the metal from the base of the ladle, the impurities are not poured into the mould. The same idea is behind the bottom pour process (Sharma, 2001).

2.5.3 Lip-Axis Design

Lip-axis ladles may also use hydraulic rams to tilt the ladle. The largest ladles are un-gearred and are typically poured using a special, two-winch crane, where the main winch carries the ladle while the second winch engages a lug at the bottom of the ladle. Raising the second winch then rotates the ladle on its trunnions. Lip-axis ladles have the pivot point of the vessel as close to the tip of the pouring spout as can be practicable. Therefore, as the ladle is rotated the actual pouring point has very little movement. Lip-axis pouring is often used on molten metal pouring systems where there is a need to automate the process as much as possible and the operator controls the pouring operation at a remote distance (Sharma, 2001).

2.5.4 Bottom Pour Design

For bottom pour ladles, a stopper rod is inserted into a tapping hole in the bottom of the ladle. To pour metal, the stopper is raised vertically to allow the metal to flow out the bottom of the ladle. To stop pouring, the stopper rod is inserted back into the drain hole. Large ladles in the steelmaking industry may use slide gates below the tap-hole (Sharma, 2001).

Medium and large ladles which are suspended from a crane have a bail which holds the ladle on shafts, called [trunnions](#). To tilt the ladle a gearbox is used and this is typically a [worm](#)

[gear](#). The gear mechanism may be hand operated with a large wheel or may be operated by an electric motor or pneumatic motor. Powered rotation allows the ladle operator to be moved to a safe distance and control the rotation of the ladle via a pendant or radio remote control. Powered rotation also allows the ladle to have a number of rotation speeds which may be beneficial to the overall casting process. Powered rotation obviously also reduces the effort required by the ladle operator and allows high volumes of molten metal to be transferred and poured for long periods without operator fatigue.

2.6 Review of Related Past Works

Ndaliman and Pius (2017), stated that “Specific casting parameters such as pouring temperatures, rate of pouring, fluidity and composition of metals are of topmost importance for consideration if sound casting is to be achieved.” They concluded that the optimum pouring temperature for Aluminium alloy was in the range of 700⁰C and 750⁰C, while the pouring speed ranged between 2.0 cm/s and 2.8 cm/s.

Peter (2001), stated that cold shuts are more serious, the discontinuity extending completely through a casting member in which streams of metal have converged from different directions. A contributing cause to these defects can be an inadequate rate of mould filling relating to the freezing rate of the casting which is a function of pouring temperature and speed. He concluded that slow mould filling may result from low pouring speed and the main rules in pouring are to maintain a smooth and uninterrupted flow of metal for the avoidance of cold shuts.

According to Yoshiyuki and Kazuhiko (2007), casting industry sometimes uses a pouring process in which molten metal is poured from a ladle into a mould by tilting the ladle. Since the process involves high-temperature molten metal, the process creates a dangerous environment for workers. Therefore, an automatic pouring system has recently been exploited to improve the working environment. The pouring process requires that the molten metal is

poured quickly and precisely into the mould and is not spilled over the sprue cup or basin. It was discovered that the proposed control system can improve the accuracy of the flow rate, and enables flow rate control to be designed systematically for the various types of ladles used in casting plants.

Robinson (2012), investigated the effect of runner size, mould temperature and pouring temperature on the mechanical properties of Aluminium alloy part produced through sand casting. He observed that the pouring temperature significantly affect the mechanical properties of sand cast aluminium alloy. Ultimate strength, hardness and elongation increases in pouring temperature.

2.7 Knowledge Gap

From the above review, it can be seen that literatures on improved pouring ladle is scarce. Hence, this study is set to fill the gap.

CHAPTER THREE

MATERIALS AND METHODS

3.1 Description of the Pouring Ladle Machine

The ladle machine consisted of the following as shown in Figure 3.1:

Gripping system: The gripping system holds the crucible firmly as it picks the crucible from the crucible pit furnace. As it holds the crucible, it is also flexible so as to allow the crucible to be tilted for pouring. The gripping system consists of the following components; chains, fork lift system, bearing cones, bearing seats.

Lifting/lowering mechanism: This mechanism allows for the lifting of the gripped crucible from the pit furnace and lowering it to the height of the sprue basin of the mould for pouring. The lifting and lowering is controlled manually using the crank lever arm and helical gears which turns a one (1) tonne chain hoist. The components of this system are as follows; lifting/lowering guide angle irons, chain hoist drive mechanism, bearings, helical gear drive system, keys, shafts, lifting/lowering lever crank handle, metal plate, bearing seat.

Tilting mechanism: This mechanism is used for the tilting of the crucible to pour the molten metal from the crucible. The tilting is done by using the crank lever arm and helical gears to turn a shaft and link mechanism which in turn tilts the gripping arm for the pouring. After the pouring, the crank lever could be used to tilt upright the crucible. This mechanism has the following components; tilting lever crank handle, helical gear system, tilting link mechanism, keys, shafts, bearings, bearing seats.

Rail mechanism: The rail mechanism helps the movement/sliding of the gripping system, lifting/lowering and tilting mechanisms from one point to another linearly i.e. from the point of pit furnace position to point of sprue basin position. The movement/sliding could be achieved by moving/sliding a system of bearings on an I-beam. The various components of the rail mechanism are as follows; rail track (I-beam), metal plate, bearings, angle irons to guide the lifting/lowering guide angle irons.

Machine frame: This is the frame that houses the machine. The frame can be moved linearly so as to allow for the pouring of molten metal from the crucible into several moulds arranged linearly. This movement could be done using the bearing sliding into the U-channel beam. The following are the components of the machine frame; standing frame, roof frame, base frame, bearings, U-channel beams, machine concrete floor and walls.

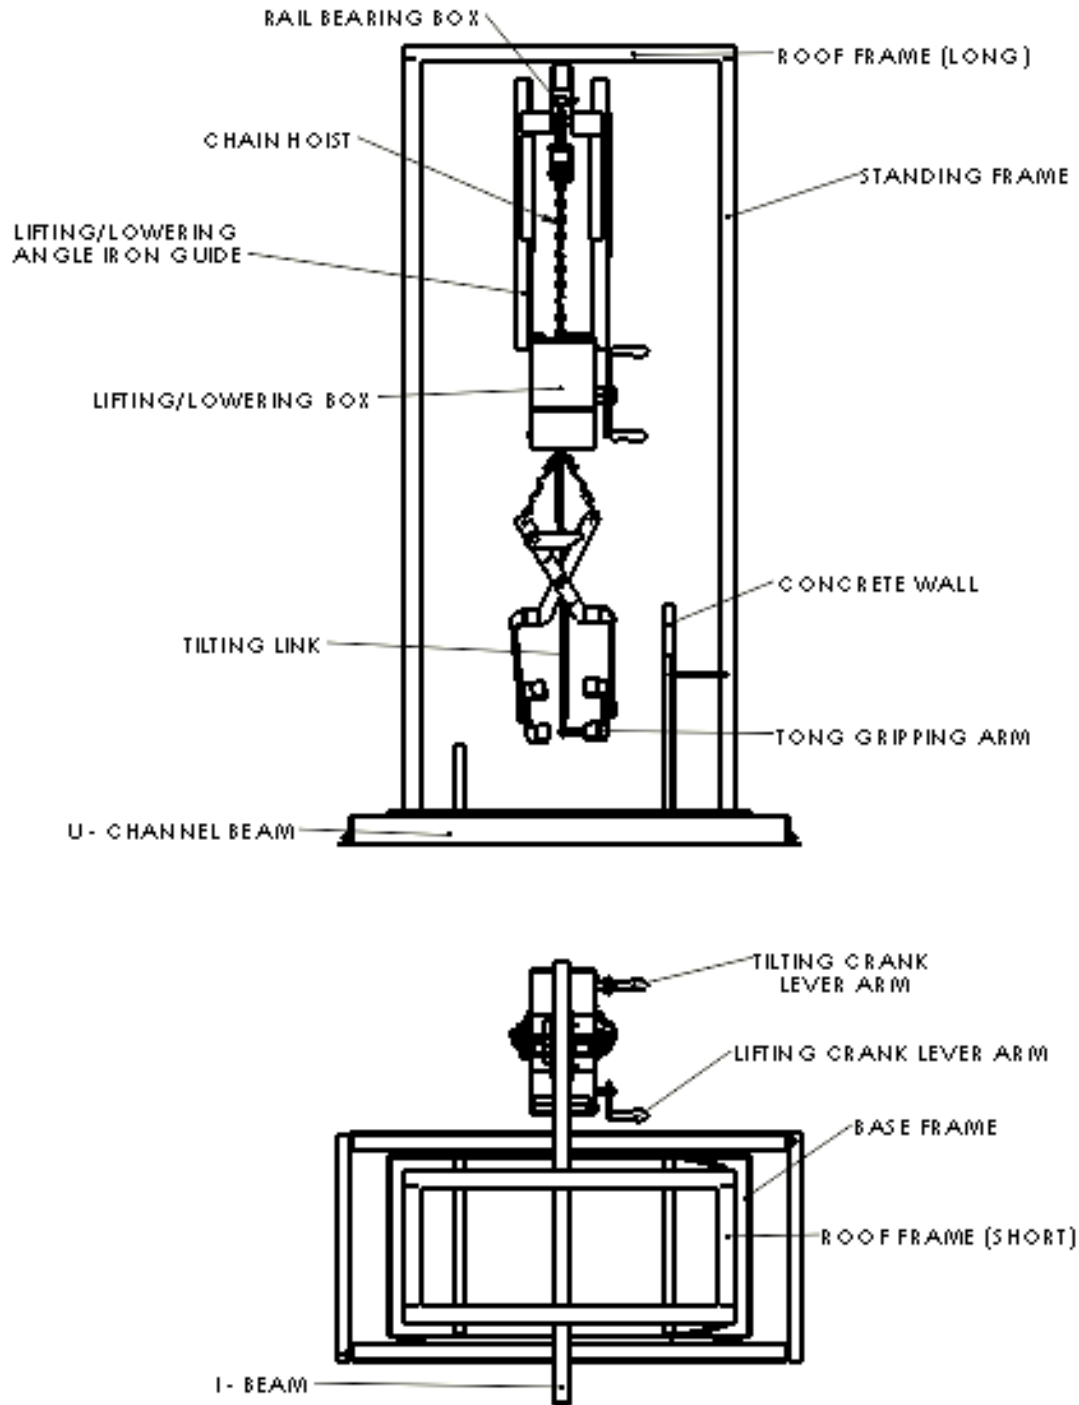


Figure 3.1: Sketch (Orthographic views) of the Casting Pouring Ladle Machine

3.2 Design Consideration

The following factors are considered in the design of the machine:

- 1) Specification: The capacity of the machine is for a crucible with 50 kg molten Aluminium alloy. Since the crucible is to hold 50 kg of molten Aluminium alloy, the tong gripping arm was forged to hold/grip the crucible. This accounts for the specification of the pouring ladle to be for 50 kg molten Aluminium alloy charge capacity.
- 2) Compact design: The machine was designed to be simple and operated manually by turning the crank lever arm manually for lifting/lowering and/or for tilting to pour the liquid metal.
- 3) Mobility: The machine was designed to be mobile (linearly) so that pouring into several moulds can be carried out from a single crucible especially if the crucible charge capacity can accommodate several castings to be produced. The mould should be arranged linearly.
- 4) Environment: The environment in which the pouring ladle would be used is the foundry. The ladle would be used to pick and hold a hot crucible containing molten Aluminium alloy inside it. Since the pouring ladle machine was not to be slid over an overhead rail and there are sands on the floor, the bearings for the mobility (through sliding) were protected from the sand particles in a U-channel beam.
- 5) Ergonomics: The pouring ladle was to be used by adults, ergonomics was considered in the design of the ladle especially in the height, crank lever arm, etc. of an average height adult.
- 6) Safety: Safety was also considered in the design and fabrication of the ladle. The arms of the gripping tong were forged to firmly grip the crucible with some extensions of rods to guard the crucible during pouring. Also, the concrete walls and sand at the floor of the machine base were to protect the operator's feet/body against any molten

metal splash in case it occurs. Furthermore, sharp edges and corners were avoided to protect the operator against injury.

- 7) **Material selection:** The materials used were carefully selected, with their availability, machinability, interchangeability, mechanical properties and thermal properties considered.
- 8) **Cost of design and construction:** This accounts for the cost incurred in the design and fabrication of the machine. The costs are material cost, labour cost and cost of maintenance.
- 9) **Maintenance:** Maintenance was considered in the design and fabrication of the ladle because most of the components were locally sourced. Some of the components such as bearings, helical gears and their keys can easily be purchased and replaced if worn out. While some components such as shaft, angle iron etc. could be purchased and machined/fabricated to the dimensions and used to replace worn out/failed components. The maintenance of the ladle does not require a special skill or rigorous procedure because applying grease to contact surfaces such as gears and bearings is not difficult to do.

3.3 Design Theory and Procedure of the Pouring Ladle and its Components

3.3.1 Design of the Tong Gripping System

The gripping system is used for holding firmly the hot crucible and molten metal as it lifts them from the pit furnace up to the point of pouring and after pouring.

3.3.1.1 **Design of Shaft Design:** This shaft connects the gripping arm and tong system. The shaft was designed to be free to rotate as one end is fixed.

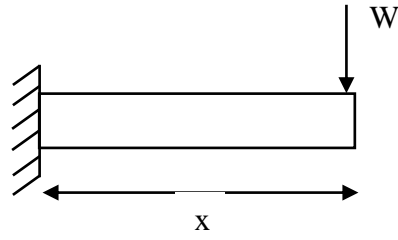


Figure 3.2: Schematic Diagram of the Shaft

The bending moment M of the shaft is given by (Khurmi and Gupta, 2005 and Rajput, 2013)

$$M = Wx \quad (3.1)$$

The bending stress σ_b is given by

$$\sigma_b = \frac{M}{Z} \quad (3.2)$$

Where the section modulus Z for the shaft is given by $Z = \frac{\pi d^3}{32}$ (3.3)

The shear stress τ on shaft cross section is given by

$$\tau = \frac{P_t}{A_r} \quad (3.4)$$

The shear strain ϕ_s is given by

$$\phi_s = \frac{\tau}{G} \quad (3.5)$$

The thermal σ_{th} stress is given by

$$\sigma_{th} = \alpha_{te} t_{rf} E \quad (3.6)$$

Where: $W =$ Weight (N)

$x =$ Length of shaft (mm)

$d =$ Diameter of shaft (mm)

$P_t =$ Tangential force (N)

$A_r =$ Resisting Area (mm^2)

$G =$ Modulus of rigidity (kN/mm^2)

$\alpha_{te} =$ coefficient of thermal expansion

$t_{rf} =$ Rise or fall in temperature ($^{\circ}\text{C}$)

$E =$ Young's Modulus (kN/mm^2)

3.3.2 Design of the Lifting/lowering Mechanism

The lifting/lowering mechanism controls the lifting and lowering of the gripped hot crucible from the pit furnace and to the point of pouring quickly without delay.

3.3.2.1 Design of Shaft: The shaft transmits motion from the crank lever to the chain hoist (Shaft 5 and Shaft 7). There are other shafts that don't transmit motion, but are used to carry load. In such a case, only the maximum bending moment and deflection are computed (Shaft 2 and Shaft 4).

In Figure 3.3a below, the load (W) is applied not at the centre of the shaft. While Figure 3.3b below, the load is applied at the centre of the shaft.

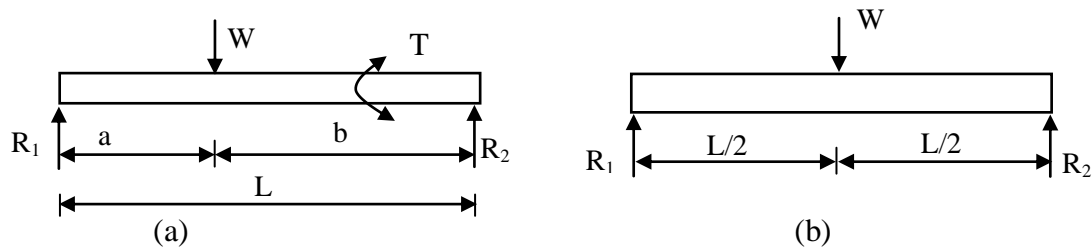


Figure 3.3: Schematic Diagram of Shafts

The torque T transmitted by shaft is given by (Khurmi and Gupta, 2005 and Rajput, 2013)

$$T = \frac{\tau x J}{r} \quad (3.7)$$

$$\text{Maximum bending moment } M = \frac{WL}{4} \quad (3.8)$$

$$\text{Or } M = \frac{Wab}{L} \quad \text{for a point load that is not at the centre} \quad (3.9)$$

$$\text{Maximum deflection can be calculated as } Y = \frac{WL^3}{48EI} \quad (3.10)$$

$$\text{Or } Y = \frac{Wa^2b^2}{3EI} \quad \text{for a point load that is not at the centre} \quad (3.11)$$

Where: J = Polar moment of inertia (mm⁴) r = Radius of the shaft (mm)

L = Total length of shaft (mm) W = Load on the shaft (N)

a = Length of shaft from one end (mm) b = Length of shaft from the other end (mm)

3.3.2.2 Design of Crank lever: The crank lever was used to transmit rotational motion from the operator to the chain hoist to lift or lower the gripped crucible through the gears and shafts.

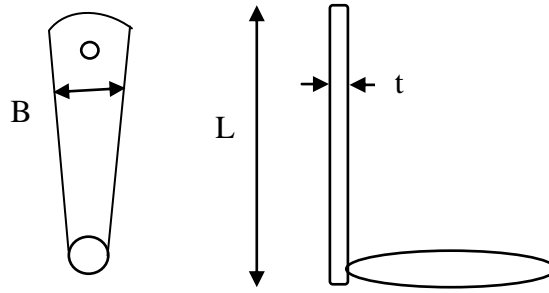


Figure 3.4: Schematic Diagram of Crank Lever Arm

For the design of the crank lever, the maximum bending moment M is given by (Khurmi and Gupta, 2005)

$$M = 1.25 WL \quad (3.12)$$

Where the shear modulus for the lever arm Z is given by $Z = \frac{t B^2}{6}$ (3.13)

The permissible bending stress σ_b is given by

$$\sigma_b = \frac{M}{Z} \quad (3.14)$$

The twisting moment $T_m = \frac{2WL}{3}$ (3.15)

And the shear stress τ is given by

$$\tau = \frac{16 T_m}{\pi d^3} \quad (3.16)$$

Where: W = Weight/load (N)

L = Length of crank lever (mm)

t = Thickness of lever (Nm)

B = Width of lever arm(mm)

d = Diameter of lever arm shaft (mm)

3.3.3 Design of the Tilting Mechanism

The tilting mechanism was design to aid the tilting of the gripped crucible for pouring as well as tilting upright of the same after pouring. The control could be carried out using the crank lever to rotate a set of two helical gears. The shaft of the lever bears the small gear the other

shaft bears the big gear and link mechanism pipe. The other link mechanism pipe was connected freely to the lower part of the gripping arm.

The designs of the components are as follows.

3.3.3.1 Design of Crank lever: The equations for the design of this crank lever is same as those of the lifting/lowering crank lever. i.e. same as equations. 3.12 to 3.16

3.3.3.2 Design of Shaft: The design equations for the design of these shafts are similar to those of lifting/lowering mechanism. i.e. same as equations. 3.7 to 3.11

3.3.4 Design of the Railing Mechanism

The rail mechanism was designed to permit the movement or sliding of the gripping system as well as the lifting/lowering and tilting mechanisms. The rail box housing houses a set of four (4) bearings on four (4) short shafts and a shaft which holds the chain hoist hook.

3.3.4.1 Design of Rail track: The rail track is the I-beam which allows the bearings of rail box housing to slide freely. The rail track was centralized on the longer roof frame with both ends of the track as over hangs.

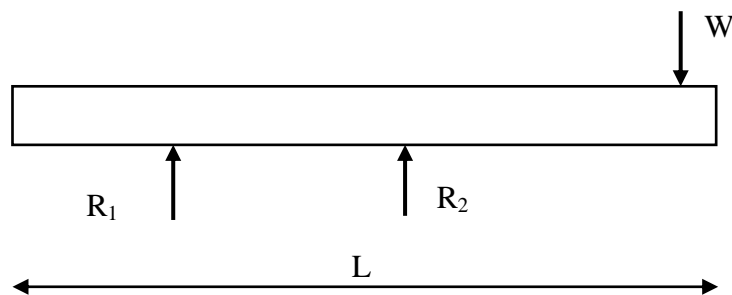


Figure 3.5: Schematic Diagram of I-Beam

For the design of the track, the maximum bending moment M at the fixed end is given by (Rajput, 2013)

$$M = WL \quad (3.17)$$

While the maximum deflection Y at the free end is given by

$$Y = \frac{WL^3}{3EI} \quad (3.18)$$

Where: W = Weight/load (N)

L = Length of hang over I-beam (mm)

E = Young's Modulus (kN/mm²)

I = Moment of inertia (mm⁴)

Design of Shaft: The shaft was fixed/welded at one end while the other free. The bearing was fixed at the free end. The design of the shaft was same as equations 3.1 to 3.5

3.3.4.2 Design of Metal plate: The metal plate was used for the rail box housing. See Figure 3.6.

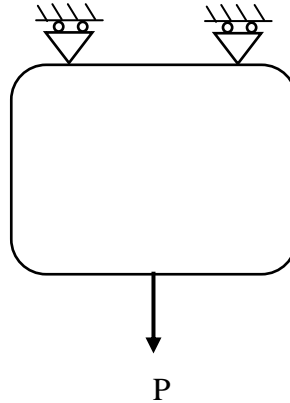


Figure 3.6: Schematic Diagram of the Plate

The tensile strength σ_T is given by (Khurmi and Gupta, 2005)

$$\sigma_T = \frac{P}{A} \quad (3.19)$$

Where: W = Weight (N)

A = Cross sectional Area (mm²)

3.3.5 Design of the Machine frame

The machine frame consisted of the parts which houses the machine. Hollowed pipes and angle irons were used for the machine frame. The hollowed pipe was used for the standing and roof frame while the angle iron for the base frame. The roof frame carries the rail track while the base frame carries the concrete floor and wall.

3.3.5.1 Design of Standing frame: The hollowed pipe was used for the standing frame which carries the roof frame with other attachment and base frame.




Figure 3.7: Schematic Diagram of Standing Frame

The compressive strength σ_C of the frame is given by (Khurmi and Gupta, 2005)

$$\sigma_C = \frac{P}{A} \quad (3.20)$$

3.3.5.2 Design of Roof frame: The roof frame was welded to the standing frame and the rail track which carries the lifting/lowering mechanism, tilting mechanism and tong gripping system. The theoretical design of the frame is same as equations. 3.8 and 3.10.

3.3.5.3 Design of Base frame: The angle iron forms the base frame which carries the concrete floor and wall. The angle irons were welded together to form a rectangular frame and also welded to the bottom of the standing frame. The theoretical design of the frame is same as equations 3.20.

3.3.6 Factor of Safety

The factor of safety (FOS) of the machine can be calculated using the equation (Khurmi and Gupta, 2005)

$$\text{FOS} = \frac{\text{Yield point stress}}{\text{working or design stress}} \quad (3.21)$$

3.4 Results of Design Calculations

Table 3.1: Design calculations for the components of the ladle machine

Initial Data	Calculations	Results
3.4.1 Tong gripping system		
$W = 392.4 \text{ N}$	i. Shaft: Using eqs. 3.1 to 3.6 for the shaft design	
$x = 10 \text{ mm}$	$M = Wx = 392.4 \times 0.5 \times 10 = 1,962 \text{ Nmm}$	$M = 1,962 \text{ Nmm}$
$d = 24 \text{ mm}$	$Z = \frac{\pi d^3}{32} = \frac{3.142 \times 24^3}{32} = 1,357.1680 \text{ mm}^3$	
$P_t = 392.4 \text{ N}$	$\sigma_b = \frac{M}{Z} = \frac{1962}{1357.1680} = 1.4457 \text{ N/mm}^2$	$\sigma_b = 1.4457 \text{ N/mm}^2$
$G = 80 \text{ kN/mm}^2$		
$t_{rf} = 750 \text{ }^\circ\text{C}$	$\tau = \frac{P_t}{A_r} = \frac{392.4}{3.142 \times 12^2} = 0.8674 \text{ N/mm}^2$	$\tau = 0.8674 \text{ N/mm}^2$
$E = 200 \text{ kN/mm}^2$	$\sigma_s = \frac{\tau}{G} = \frac{0.8674}{80 \times 10^3} = 1.0843 \times 10^{-5}$	$\sigma_s = 1.0843 \times 10^{-5}$
$\alpha = 11.7 \times 10^{-6}$	$\sigma_{th} = \alpha t_{rf} E = 11.7 \times 10^{-6} \times 750 \times 200 \times 10^3$	
per $^\circ\text{C}$	$= 1.755 \text{ kN/mm}^2$	$\sigma_{th} = 1.755 \text{ kN/mm}^2$
3.4.2 Lifting/Lowering mechanism		
$W = 3.924 \text{ N}$	i. Shaft: Using eqs. 3.7 to 3.11 for the shaft design. For	
$d = 17 \text{ mm}$	shaft 5, torque transmitted is	
$a = 80 \text{ mm}$	$T = \frac{\tau x J}{r} = \frac{0.0173 \times 8199.6550}{8.5} = 16.6887 \text{ Nmm}$	$T = 16.6887 \text{ Nmm}$
$b = 122 \text{ mm}$	$M = \frac{Wab}{L} = \frac{3.924 \times 80 \times 122}{202} = 189.5952 \text{ Nmm}$	$M = 189.5952 \text{ Nmm}$
$E = 200 \text{ kN/mm}^2$	$Y = \frac{Wa^2b^2}{3EI} = \frac{3.924 \times 80^2 \times 122^2}{3 \times 200 \times 10^3 \times 4099.8275} = 0.1520 \text{ mm}$	$Y = 0.1520 \text{ mm}$
	For shaft 7, the torque, maximum bending moment and	
	deflection is	$T = 3.8723 \text{ Nmm}$
$a = 50 \text{ mm}$	$T = \frac{\tau x J}{r} = \frac{0.005 \times 6118.2644}{7.9} = 3.8723 \text{ Nmm}$	$M = 19.5018 \text{ Nmm}$
$b = 33 \text{ mm}$	$M = \frac{Wab}{L} = \frac{0.981 \times 50 \times 33}{83} = 19.5018 \text{ Nmm}$	$Y = 0.0015 \text{ mm}$
$d = 15.8 \text{ mm}$	$Y = \frac{Wa^2b^2}{3EI} = \frac{0.981 \times 50^2 \times 33^2}{3 \times 200 \times 10^3 \times 3059.1322} = 0.0015 \text{ mm}$	
Initial Data		Results

Calculations

For shaft 4, the maximum bending moment and $M = 19,188.36$
deflection is Nmm

$d = 25$ mm

$$M = \frac{WL}{4} = \frac{470.88 \times 163}{4} = 19,188.36 \text{ Nmm}$$

$$Y = 0.0111 \text{ mm}$$

$$Y = \frac{WL^3}{48EI} = \frac{470.88 \times 163^3}{48 \times 200 \times 10^3 \times 19,174.7599} = 0.0111 \text{ mm}$$

For shaft 2, the maximum bending moment and $M = 16,414.5825$
deflection is Nmm

$d = 21$ mm

$$M = \frac{WL}{4} = \frac{676.89 \times 97}{4} = 16,414.5825 \text{ Nmm}$$

$$Y = 6.7409 \text{ mm}$$

$$Y = \frac{WL^3}{48EI} = \frac{676.89 \times 97^3}{48 \times 200 \times 10^3 \times 9,546.5638} = 6.7409 \text{ mm}$$

ii. Crank lever: for the big (lifting/lowering) crank lever
arm, using eqs. 3.12 to 3.16 for the design, the maximum
bending moment M of the lever arm is

$$W = 98.0665 \text{ N}$$

(10 kg)

$$L = 135 \text{ mm}$$

$$d = 17 \text{ mm}$$

$$M_{\max} = 1.25 WL = 1.25 \times 98.0665 \times 135 \\ = 16,548.7219 \text{ Nmm}$$

$$M_{\max} = 16,548.7219$$

Nmm

The shear modulus for the lever arm Z is given by

$$t = 8 \text{ mm}$$

$$B = 35 \text{ mm}$$

$$Z = \frac{t B^2}{6} = \frac{8 \times 35^2}{6} = 1,633.3333 \text{ mm}^3$$

$$\sigma_b = 10.1319$$

N/mm²

The permissible bending stress σ_b

$$\sigma_b = \frac{M}{Z} = \frac{16548.7219}{1633.3333} = 10.1319 \text{ N/mm}^2$$

The twisting moment

$$T_m = \frac{2WL}{3} = \frac{2 \times 98.0665 \times 135}{3} = 8,825.985 \text{ Nmm}$$

$$\tau = 9.1493 \text{ N/mm}^2$$

and the shear stress τ is

$$\tau = \frac{16 T_m}{\pi d^3} = \frac{16 \times 8825.985}{3.142 \times 17^3} = 9.1493 \text{ N/mm}^2$$

Initial Data	Calculations	Results
3.4.3 Tilting Mechanism		
W = 98.0665 N (10 kg)	i. Crank lever: for the design of the small (tilting) crank lever arm, using eqs. 3.12 to 3.16, the maximum bending moment M of the lever arm is	
L = 106 mm		
d = 15.8 mm	$M_{\max} = 1.25 WL = 1.25 \times 98.0665 \times 106$ $= 12,993.8113 \text{ Nmm}$	$M_{\max} = 12.9938$ kNmm
t = 8 mm	The shear modulus for the lever arm Z is given by	
B = 35 mm	$Z = \frac{t B^2}{6} = \frac{8 \times 35^2}{6} = 1,633.3333 \text{ mm}^3$ The permissible bending stress σ_b $\sigma_b = \frac{M}{Z} = \frac{12993.8113}{1633.3333} = 7.9554 \text{ N/mm}^2$	$\sigma_b = 7.9554 \text{ N/mm}^2$
	The twisting moment $T_m = \frac{2WL}{3} = \frac{2 \times 98.0665 \times 106}{3} = 6,930.0327 \text{ Nmm}$ and the shear stress τ is $\tau = \frac{16 T_m}{\pi d^3} = \frac{16 \times 6930.0327}{3.142 \times 15.8^3} = 8.9482 \text{ N/mm}^2$	$\tau = 8.9482 \text{ N/mm}^2$
	ii. Shaft: Same as eqs. 3.7 to 3.11 for shaft 8, torque transmitted is	
d = 15.8 mm	$T = \frac{\tau \times J}{r} = \frac{0.0050 \times 6118.2644}{7.9} = 3.8723 \text{ Nmm}$	T = 3.8723 Nmm
a = 132 mm	$M = \frac{Wab}{L} = \frac{0.981 \times 132 \times 67}{199} = 43.5978 \text{ Nmm}$	M = 43.5978 Nmm
b = 67 mm	$Y = \frac{W a^2 b^2}{3EI} = \frac{0.981 \times 132^2 \times 67^2}{3 \times 200 \times 10^3 \times 3059.1322} = 0.0418 \text{ mm}$	Y = 0.0418 mm
L = 199 mm		
E = 200 kN/mm ²	For shaft 9, the torque, maximum bending moment and deflection is	

Initial Data	Calculations	Results
W = 3.924 N	$T = \frac{\tau \times J}{r} = \frac{0.0173 \times 8199.6550}{8.5} = 16.6887 \text{ Nmm}$	T = 16.6887 Nmm
d = 17 mm		
a = 132 mm	$M = \frac{Wab}{L} = \frac{3.924 \times 132 \times 67}{178} = 194.9655 \text{ Nmm}$	M = 194.9655 Nmm
b = 67 mm		
L = 178 mm	$Y = \frac{Wa^2b^2}{3EI} = \frac{3.924 \times 132^2 \times 67^2}{3 \times 200 \times 10^3 \times 4099.8275} = 0.1248 \text{ mm}$	Y = 0.1248 mm
3.4.4 Rail Mechanism		
	i. Rail track: Using eqs. 3.17 to 3.18,	$M_{\max 1} = 377,685$
W = 686.7 N	$M_{\max 1} = WL_1 = 686.7 \times 550 = 377,685 \text{ Nmm}$	Nmm
L ₁ = 550 mm	$M_{\max 2} = WL_2 = 686.7 \times 250 = 171,675 \text{ Nmm}$	$M_{\max 2} = 171,675$
L ₂ = 250 mm	$Y_1 = \frac{WL_1^3}{48EI} = \frac{686.7 \times 550^3}{48 \times 200 \times 10^3 \times 571850.6667} = 0.0208 \text{ mm}$	Nmm
E = 200 kN/mm ²	$Y_2 = \frac{WL_2^3}{48EI} = \frac{686.7 \times 250^3}{48 \times 200 \times 10^3 \times 571850.6667} = 0.0020 \text{ mm}$	Y ₁ = 0.0208 mm Y ₂ = 0.0020 mm
	ii. Shaft: using eqs. 3.1 to 3.5	
W = 676.89 N	The bending moment M of the shaft is	$M = 2,538.3375$
x = 15 mm	$M = Wx = 676.89 \times 0.25 \times 15 = 2538.3375 \text{ Nmm}$	Nmm
d = 25 mm	Using eq. 3.3 and 3.2, the bending stress σ_b is given by	
P _t = W	$Z = \frac{\pi d^3}{32} = \frac{3.142 \times 25^3}{32} = 1,533.9808 \text{ mm}^3$	$\sigma_b = 1.6547 \text{ N/mm}^2$
G = 80 kN/mm ²	$\sigma_b = \frac{M}{Z} = \frac{2538.3375}{1,533.9808} = 1.6547 \text{ N/mm}^2$	
	$\tau = \frac{P_t}{A_r} = \frac{676.89}{4 \times 3.142 \times 8.5^2} = 0.7455 \text{ N/mm}^2$	$\tau = 0.7455 \text{ N/mm}^2$
	the shear strain is	
P = 678.852 N	$\phi_s = \frac{\tau}{G} = \frac{0.7455}{80 \times 10^3} = 9.3188 \times 10^{-6} \text{ N/mm}^2$	
L = 185 mm	iii. Metal plate: Using eq. 3.53, the tensile strength σ_T is	$\sigma_T = 0.3669 \text{ N/mm}^2$
b = 5 mm	$\sigma_T = \frac{P}{A} = \frac{678.852}{2 \times 185 \times 5} = 0.3669 \text{ N/mm}^2$	

Initial Data	Calculations	Results
	3.4.5 Machine frame	
	i. Standing frame: Using eq. 3.39, the compressive	
D = Ø48 mm	strength σ_C is	
d = Ø41 mm	$\sigma_C = \frac{P}{A} = \frac{1196.82}{4 \times 3.142 \times (24^2 - 20.5^2)} = 0.6115 \text{ N/mm}^2$	$\sigma_C = 0.6115 \text{ N/mm}^2$
P = 1,196.82 N		
	ii. Roof frame: Using eqs. 3.8 and 3.10, the maximum	
W = 735.75 N	bending moment M_{\max} is	
L = 920 mm	$M_{\max} = \frac{WL}{4} = \frac{735.75 \times 0.5 \times 920}{4} = 84,611.25 \text{ Nmm}$	$M_{\max} = 84,611.25$
E = 200 kN/mm ²		Nmm
	Maximum deflection	
l = 992mm	$Y = \frac{WL^3}{48EI} = \frac{735.75 \times 0.5 \times 920^3}{48 \times 200 \times 10^3 \times 121867.0423} = 0.2449 \text{ mm}$	Y = 0.2449 mm
b = 492 mm		
P = 402.21N	iii. Base frame: Using eq. 3.9	$\sigma_C = 8.2409 \times 10^{-4}$
	$\sigma_C = \frac{P}{A} = \frac{402.21}{992 \times 492} = 8.2409 \times 10^{-4} \text{ N/mm}^2$	N/mm ²
$\sigma_y =$	3.4.6 Factor of safety of the machine	FOS = 2
2.5299N/mm ²	$\text{FOS} = \frac{\text{Yield point stress}}{\text{working or design stress}} = \frac{2.5299}{1.4457} \approx 2$	
$\sigma_w =$		
1.4457N/mm ²		

3.5 Selection of Materials for the Fabrication and Assembly of the Pouring Ladle Machine

The choice of materials was carefully considered since the machine would be used to cast molten Aluminium metal. Most or majority of the component parts (hollowed pipe, metal plate, bar, rod, U-channel beam, I-beam, angle iron) were purchased at the “Yan karfe” market in Zaria, chain hoist (1 tonne) was purchased at Kakuri market, cement, stones and

helical gears at Samaru and bearing at Tudun wada Zaria. Below are tables (Table 3.2 to Table 3.6) listing the various components of the machine.

3.5.1 The Tong Gripping System

Table 3.2: Material components of tong gripping system

S/N	COMPONENT	MATERIAL	DESCRIPTION
1	Chains	Mild steel	Standard component
2	Fork lift	Mild steel	Mild steel bar, purchased and fabricated
3	Bearing inner cone	Stainless steel	Standard component
4	Bearing seat	Mild steel	Mild steel pipe, purchased and fabricated

3.5.2 The Lifting/lowering Mechanism

Table 3.3: Material components of lifting/lowering mechanism

S/N	COMPONENT	MATERIAL	DESCRIPTION
1	Lifting/lowering guide angle irons	Mild steel	Mild steel angle iron, purchased and fabricated
2	Chain hoist	Mild Steel	Standard
3	Bearings	Stainless steel	Standard
4	Helical gear system	Medium carbon steel	Standard
5	Keys	Mild steel	Standard
6	Shafts	Mild steel	Mild steel rod, purchased and fabricated
7	Lifting/lowering crank lever	Aluminium alloy	Cast
8	Metal plate	Mild steel	Mild steel plate, purchased and fabricated
9	Bearing seat	Mild steel	Mild steel pipe, purchased and fabricated

3.5.3 The Tilting Mechanism

Table 3.4: Material components of tilting mechanism

S/N	COMPONENT	MATERIAL	DESCRIPTION
1	Tilting crank lever	Aluminium alloy	Cast
2	Helical gear system	Medium carbon steel	Standard
3	Tilting link mechanism	Mild steel	Mild steel pipe, purchased and fabricated
4	Keys	Mild steel	standard
5	Shafts	Mild steel	Mild steel rod, purchased and fabricated

3.5.4 The Railing Mechanism

Table 3.5: Material components of railing mechanism

S/N	COMPONENT	MATERIAL	DESCRIPTION
1	Rail track (I-beam)	Mild steel	Mild steel I-beam, purchased and fabricated
2	Metal plate	Mild steel	Mild steel plate, purchased and fabricated
3	Bearings	Stainless steel	Standard
4	Angle iron	Mild steel	Mild steel angle iron, purchased and fabricated

3.5.5 Machine Frame

Table 3.6: Material components of machine frame

S/N	COMPONENT	MATERIAL	DESCRIPTION
1	Standing frame	Mild steel	Mild steel pipe, purchased and fabricated
2	Roof frame	Mild steel	Mild steel pipe, purchased and fabricated
3	Base frame	Mild steel	Mild steel angle iron, purchased and fabricated
4	Bearings	Stainless steel	Standard
5	U-channel beam	Mild steel	Mild steel U-channel beam, purchased and fabricated
6	Machine concrete floor	Metal rods, cement, sand, gravels and water	Cast

3.6 Fabrication and Assembly of the Pouring Ladle

3.6.1 Fabrication Process Plan of the Ladle Components

Some components of the pouring ladle machine were purchased from the market and used directly such as helical gears and keys, bearing etc. while others such as angle iron, hollowed pipe, metal plate, bar, rod, etc. were fabricated based from the design calculation in Table 3.1. These machines and tools used for the fabrication are from the National Automotive Design and Development Council (NADDC) Zaria and are listed below.

- i. Electric arc welding machine
- ii. Hand hacksaw
- iii. Lathe machine (Model: TOS Trencin SN. 32, SCH: 307982823)
- iv. Horizontal Milling machine (Model: FA3B, No. 332000666)
- v. Vertical drilling machine (Model: Boxford Model No. CF18)
- vi. Hand grinding/cutting machine
- vii. Forging tools (anvil and hammer)
- viii. Vices and clamps
- ix. Weighing scales to measure the weight of crucible, Aluminium allot scraps, some components of the ladle

The fabrication process plan of the pouring ladle is as shown in Table 3.7 below.

Table 3.7: Fabrication process plan of the pouring ladle and the tools/machines used

S/N	Component	Description	Tools/Machines
1	Tong guide	<ul style="list-style-type: none"> Cut 2 pieces of metal plates and flat bar. Drill one end of the plates and weld the flat in between the plates for M12 bolt and nut (Appendix A, Drawing No. 7). 	Hand cutting machine, Hack saw, Forging hammer, Anvil,
	Tong gripping system	<ul style="list-style-type: none"> Cut flat bars, forge and weld to form the “X” shape gripping tong. Cut and weld the inner bearing seat to the lower end of the gripping tong. Fix the bearing cone inside the bearing seat. Drill holes on the upper end and weld chain to the holes. Fasten bolt and nut to hinge the two halves of the bars (Appendix A, Drawing No. 7). Weld chains to the upper part of the gripping tong and also weld a hook to the free end of the chains. Attach the hook to the shaft 4 on the gear box housing. 	Charcoal furnace, Lathe machine, Electric arc welding machine, Vice and Clamps, Hand files
	Gripping arm	<ul style="list-style-type: none"> Cut flat bars (8 pcs), forge and weld to another flat bar to form an “H” shaped gripping arm. On the middle of the flat bar, weld a shaft to enter the inner bearing cone. Cut and weld a rod on one flat bar of the lower arm which will link with the tilting link pipe (Appendix A, Drawing No. 6. i.e right and left part of tong gripping arm) 	
2	Lifting/ lowering box	<ul style="list-style-type: none"> Cut metal plates (2 similar pcs and a dissimilar piece), cut and weld two pcs of galvanized pipe on one side of the similar plate. While on the other plate, drill a hole to allow the welded bolt on the other end to pass through. Cut, machine and weld bearing seat on the inner sides of the plates. Drill holes on the plates. Cut, machine and weld one end of shaft 2 and 3 and 4 on one side 	Hand cutting machine, Hack saw, Lathe machine, Milling machine, Electric arc welding machine, Vice and Clamps,

S/N	Component	Description	Tools/Machines
Lifting/lowe ring crank lever and shaft		<p>of the similar plate (Appendix A, Drawing No. 5, 6, and 7).</p> <ul style="list-style-type: none"> Cut 2 pcs of angle irons (730 mm) and weld to the outside part of the similar plates. Cut and weld <p>3pipes on one side of the middle plate (the dissimilar plate) and a shaft on the opposite side of the plate. Drill Ø30 mm hole to allow for the shaft 7 to pass through. Weld bearing seat on one side of the plate (Appendix A, Drawing No. 5).</p> <ul style="list-style-type: none"> Cut and machine shaft 5, weld key slot (Appendix A, Drawing No. 5 and 7)for bigger gear on the shaft. Cast lever crank handle with Aluminium alloy metal using sand casting method (Appendix A, Drawing No. 7). Fasten the lever crank handle firmly to the shaft 5 using the bolt and nut. Fix the big gear to the shaft. Cut and machine shafts 6 and 7. Drill hole on shaft 7. Weld key slot for bigger gear on shaft 6. Machine key ways on both shafts.Fix both bigger and smaller gears and keys on shaft 6 while a smaller gear on shaft 7 (Appendix A, Drawing No. 7). 	Hand files
3 Tilting link Tilting crank lever and		<ul style="list-style-type: none"> Cut and machine shaft 9. Cut and weld pipe (pipe has both ends flattened and a hole drilled). Weld one of the pipes (short) to the shaft and the key slot for bigger gear on the shaft. Fix the bigger gear on the shaft. Fasten the two pipes (linking pipes) using an M10 bolt and nut. Attached the free end of the linking pipe to the rod at the base arm of the tong gripping arm (Appendix A, Drawing No. 6). Cut and machine shaft 8and weld a bolt on one end. Machine key way on the shaft. Fix a small 	Hand cutting machine, Hack saw, Lathe machine, Milling machine, Electric arc welding machine, Vice and Clamps, Hand files

shaft helical gear and key to the shaft. Fix the small cast crank handle using the bolt and nut (Appendix A, Drawing No. 6).

S/N	Component	Description	Tools/Machines
4	I-beam frame Rail box (left and right part of rail box)	<ul style="list-style-type: none"> Cut I-beam and weld to the roof frame of the machine frame (Appendix A, Drawing No. 4). Cut 2 pcs of metal plates, pipes (2 pcs) and shafts (4 similar pcs) and shaft 1. Weld the shafts and galvanized pipe on one side of one of the metal plate. Drill holes on the other plate (Appendix A, Drawing No. 4). Cut smaller metal plates (4 pcs), shafts (2 pcs) and angle irons (4 pcs). Weld a shaft on one side of a plate while the other side, weld two angle irons. On the other plate weld two angle irons on one side. Weld these plates to the other sides (outer side) of the left and right metal plates above (Appendix A, Drawing No. 4) Attached/hook the chains hoist hook (from the lifting/lowering gear box housing) on shaft 1. 	Hand cutting machine, Hack saw, Lathe machine, Milling machine, Electric arc welding machine, Vice and Clamps, Hand files

5	Standing and roof frame Base frame U-channel base frame	<ul style="list-style-type: none"> • Cut 4 pcs of hollowed pipe to a length of 2140 mm and weld to other pipes i.e. long and short roof bar to form a frame (Appendix A, Drawing No. 3). • Cut and weld 4 pcs of angle iron i.e. 2 long and 2 short to form a base frame. Weld to the lower end of the standing frame. Cast a concrete floor and walls on the base frame (Appendix A, Drawing No. 3) • Cut U-channel beams (2 pcs) and angle irons (2 pcs). Weld them together to form a base frame so that the bearing on the standing frame can easily slide in the U-groove. Also weld an M10 bolt at the free end of the angle iron welded to the U-channel beam (Appendix A, Drawing No. 3). 	Hand cutting machine, Hack saw, Forging tools, Lathe machine, Milling machine, Electric arc welding machine, Vice and Clamps, Hand files, Shovel, Weighing scale,
---	---	--	---

3.6.2 Assembly of the Ladle Component Parts

The various components were assembled together to form the ladle machine. Some parts of the machine are welded for permanent joint while other parts were temporary joined using bolts and nuts so as to allow for interchangeability. The bearings for the sliding movement of the ladle at the base frame were fixed to the shafts. The bearings were the guided into the U-channel beams then screwed using bolts and nuts.

The rail box was fixed at the I-beam with the bearing freely rolling along the beam. The lifting/lowering box was then coupled and fixed to the angle iron guide of the rail box. This was to aligned and allow for the movement of the lifting/lowering system up and down. The tong gripping and tilting mechanisms were coupled together and attached to the lifting/lowering box. The hook was to hang on the shaft attached at the base of the lifting/lowering box while the tilting link was connected to the other link rod using a bolt and nut joint.

3.6.3 Principle of Operation of the Ladle

The machine was designed to be mobile through the use of the bearings to slide to the linearly array prepared moulds. The rail mechanism can be slide to one side (e.g. right) to ensure that the gripping tong is aligned to the crucible in the furnace. The lifting/lowering mechanism would be used to lower the gripping tong to make contact in form of gripping the crucible. The tong would grip the crucible using the weight of the crucible and liquid Aluminium as the lifting/lowering mechanism is lifted up from the furnace. The rail system would be used to slide the crucible to the other side (e.g. left) or middle of the machine frame. The machine would then be slide to the location of the prepared mould for pouring by using the lifting/lowering mechanism to lift or lower the crucible to the height of the pouring sprue basin and then tilt the crucible so that the molten metal will flow or pour into the mould. After pouring, the crucible would be tilted back to upright position lowered and dropped by releasing the gripping tong and placed to a suitable location (safe place) as desired.

3.6.4 Cost Analysis of the Pouring Ladle

The cost analysis or Bill of Engineering Measurement and Evaluation of the pouring ladle machine was based on the material, labour and overhead cost. The material cost comprises of the cost incurred to purchase the material from the market (see Table 3.8). The labour cost comprises of the cost incurred in cutting, machining and welding of the machine parts to form the machine. The overhead cost comprises of the cost of transportation and other miscellaneous during the process of fabrication of the machine. Tables 3.9 shows the cost evaluation of the pouring ladle machine

Table 3.8: Bill of Materials for the pouring ladle machine

S/N	Component	Material	Dimensions	Quantity	Unit Cost(₦)	Total (₦)
1	Hollowed pipe	Mild steel	5,486.4 mm length, outside diameter of Ø48 mm and inner diameter of Ø41 mm	2	4,750	9,500

2	Plate	Mild steel	1,830 mm x 610 mm x 5 mm	1	2,000	2,000
3	Shaft	Mild steel	500 mm x Ø28 mm	1	200	200
			1000 mm x Ø25 mm	1	500	500
			1100 mm x Ø21 mm	1	600	600
4	Concrete rod	Mild steel	1,000 mm x Ø8 mm	7	100	700
5	Quarter rod	Mild steel	500 mm x Ø5 mm	1	150	150
6	I-beam	Mild steel	1300 mm x 76 mm x 45 mm	1	1,200	1,200
7	U-Channel beam	Mild steel	48 mm x 80 mm x 5 mm of 2400 mm length	1	3,000	3,000
8	Flat bar	Mild steel	3210 mm x 40 x 10 mm	1	2,000	2,000
9	Angle iron	Mild steel	40 mm x 40 mm x 4 mm of 1200 mm length	4	250	1,000
			38 mm x 38 mm x 2 mm of 3,200 mm length	2	350	700
10	Pipe	Mild steel	Ø21 mm and Ø17 mm outside and inner diameter x 800 mm length	1	50	50
S/N	Component	Material	Dimensions	Quantity	Unit Cost (₦)	Total (₦)
			Ø16 mm and Ø12 mm outside and inner diameter x 810 mm length	2	125	250
11	Electrode	E6038	Gauge 10	1 packet	1,600	1,600
12	Cutting disc	Abrasive materials	125 x 1.2 x 22.2 mm	2	650	1,300
13	Grinding disc	Abrasive materials	Standard	2	300	600
14	Hack saw blade	High carbon steel	12 inches	3	300	900
15	Bearing	High carbon steel	Ø68 mm, Ø26 mm outside and inner diameter x 18 mm length	4	300	1,200
			Ø52 mm, Ø25 mm outside and inner diameter x 15 mm length	4	100	400

			Ø35 mm, Ø17 mm outside and inner diameter x 10 mm length	11	200	2,200
			Ø32 mm, Ø15 mm outside and inner diameter x 9 mm length	2	100	200
16	Chain hoist	Nil	1 tonne	1	4,500	4,500
17	Helical Gears and keys	Mild steel	Nil	3 each	350	1,050
18	Crank lever handle	Aluminium alloy	162 mm length x 8 mm thickness and 132 mm length x 8 mm thickness	2	300	600
19	Bolts and two nuts	Medium carbon steel	M8	1	30	30
			M10	11	30	330
			M12	1	100	100
20	Washers	Medium carbon steel	Ø39.5 mm, Ø21 mm x 2.5 mm	3	30	90
			Ø30 mm, Ø12.5 mm x 2.5 mm	4	15	60
			Ø24 mm, Ø10.5 mm x 2.5 mm	2	10	20
S/N	Component	Material	Dimensions	Quantity	Unit Cost (₦)	Total (₦)
21	Greece	Standard	200 g	1	300	300
22	Stones	Rock	Sieve size of 9.5 mm ² opening	½ bag	700	300
23	Cement	Lime stone	11.55 kg	11.55 kg	150	450
24	Austine oil Paint	Nil	4 kg	10 kg	1,600	800
25	Paint brush	Nil	Medium	1	60	60
Total Cost						38,940

Table 3.9: Labour and cost of production of the pouring ladle machine

S/N	Item	Total Cost (₦)
1	Cost of materials	38,940.00
2	Cost of labour (cutting of metal, machining, welding and fabrication etc.)	25,000.00
3	Cost of transportation and other miscellaneous	3,000.00
Grand Total Cost		66,940.00

3.7 Performance Evaluation/Testing of the Pouring Ladle Machine

3.7.1 Performance evaluation using water and Aluminium alloy molten metal

The machine was tested using water inside the crucible and poured into a five (5) L “Jerry can” through a funnel. This was carried out to first of all see how the pouring ladle machine would perform before using it for the casting of the Aluminium alloy metal. The time taken for the lifting and pouring using water was taken and recorded using both ladle machine and hand-shank ladle (see Plate V and VI, Appendix B).

Water and Aluminium were used to evaluate the ladle machine because Yoshiyuki and Kazuhiko (2007), verified the effectiveness of a proposed control system, which was applied to an automatic pouring system and was tested experimentally using both water and molten metal. Also, Aluminium flows like water and the ladle machine was designed to cast Aluminium metal.

Since the ladle machine’s performance was as desired, the machine was then used to cast the Aluminium alloy metal. The total time taken to lift the crucible from the furnace to filling the mould with the liquid Aluminium alloy metal was noted by a stop watch and recorded. The same was carried out for the manual hand-shank ladle.

The moulds for the Aluminium alloy casting were made from water jacket and bearing cap of a 4-stroke 800cc engine block, crank lever and a pipe pattern. The sand mould was used in this research because it is cheaper, most common and available at the foundry.

One of the most versatile methods is sand casting. Virtually any pattern can be pressed into a fine sand mixture to form a mould into which the aluminium could be poured. This is by far the highest productivity of any casting process, and highly economical. Variants of the process are also suitable for small quantities, intricate designs and one-off and large castings (Derya, 2005).

The casting was carried out at NADDC foundry shop. See Plate 3.1 for the pattern used and Plate 3.2a and 3.2b for the moulds used for the ladle machine and manual hand-shank ladle.



Plate 3.1: Patterns used for the production of mould for the casting



Plate 3.2a: Sand mould for pouring ladle Plate 3.2b: Sand mould for hand-shank ladle

3.7.2 Determination of the speed of pouring

The speed of pouring of Aluminium alloy molten metal using the ladle machine and manual hand-shank were calculated using the equation (Ndaliman and Pius, 2007)

$$V = \frac{H}{T_p} \quad 3.22$$

Where: H = Height from crucible to sprue basin (cm) T_p = Time taken for pouring (sec)

3.7.3 Non-destructive Test

3.7.3.1 Visual inspection of the cast

Two cast samples produced using the pouring ladle machine and hand-shank ladle pouring were visually inspected to check for misrun, cold shot and other casting defects.



Plate 3.3: Cast sample of improved casting pouring ladle



Plate 3.4: Cast sample of hand-shank ladle

3.7.3.2 Metallography examination of the cast:

A sample from both casts was cut from the solid rod with the end surface ground and polished. The preparation of both samples for the test involved mainly cutting of sample to a suitable size and shape, grinding, polishing and etching. The snap capturing was carried out using the Metallurgical microscope model NJF-1 machine (Plate 3.6) at the departmental lab of Metallurgical and Material Engineering department, A.B.U. Zaria. The samples used for the metallography test are shown in Plate 3.5 below.



Plate 3.5: Samples for metallography test. Where sample A was from pouring ladle model NJF-1 for snap capturing of the samples and sample B from hand-shank ladle

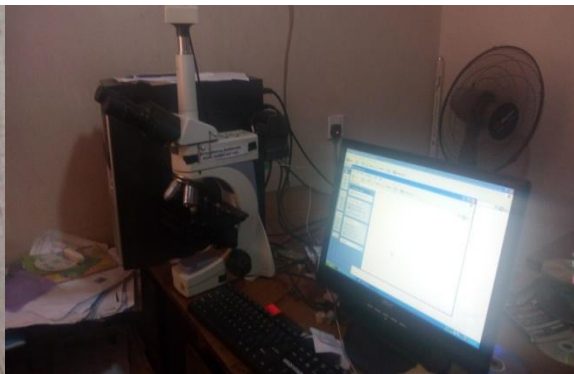


Plate 3.6: Using the metallurgical microscope

3.7.3.3 X-Ray Fluorescence (XRF) test of the cast:

The cut transverse section of samples from both casts (Plate 3.7) were mounted in contact with the lens of the XRF machine where the rays projected on the surface. Each sample was subjected to XRF test at four (4) different energy levels. The XRF test was carried out at the Centre for Minerals Research and Development, Kaduna Polytechnic and the machine model was XL3t 950 (Plate 3.8).



Plate 3.7: Samples for XRF test.
XL3t 950 for snap capturing of the sample



Plate 3.8: Using the XRF machine model XL3t 950 for snap capturing of the sample

CHAPTER FOUR

RESULTS AND DISCUSSION

4.1 Results

4.1.1 Result of the Pouring Ladle Machine

4.1.1.1 Result of Performance Evaluation using Water

For the evaluation of the ladle machine, the ladle machine was tested with water. Similarly, the same was done using the hand-shank ladle. Table 4.1 shows the pouring times for the ladle casting machine. While Table 4.2 shows that for using the hand-shank ladle.

Table 4.1: Result of Pouring Time for Ladle Machine using water

No. of trials	Time (sec)			Total Time (sec)
	Lifting & Movement	Lowering & Movement	Pouring	
1	33.05	7.97	54.69	95.71
2	30.03	8.90	50.58	89.51
3	30.97	7.54	47.73	86.24
4	28.66	8.35	51.16	88.17
5	31.09	8.59	48.51	88.19
6	31.24	8.71	50.08	90.03
7	28.98	8.83	47.22	85.03
8	30.02	7.90	50.58	88.50
9	30.71	8.41	49.37	88.49
10	29.89	8.26	49.82	87.97
AVERAGE	30.46	8.35	49.97	88.78

Table 4.2: Result of Pouring Time for Hand-shank Ladle using Water

No. of trials	Time (sec)			Total Time (sec)
	Lifting & Movement	Lowering & Movement	Pouring	
1	36.68	40.01	49.93	126.62
2	30.51	37.04	51.09	118.64
3	31.72	34.83	50.95	117.50
4	34.16	36.96	54.38	125.50
5	30.69	37.90	50.84	119.43
6	33.30	35.17	49.35	117.82
7	34.12	35.31	51.77	121.20
8	31.73	34.79	50.20	116.72
9	32.55	34.63	50.08	117.26
10	32.13	36.28	52.14	120.55
AVERAGE	32.76	36.29	51.07	120.12

4.1.1.2 Result of Performance Evaluation using Aluminium Alloy

Result of the casting of the Aluminium alloy molten metal are given in Tables 4.3 and 4.4.

Table 4.3: Result of Pouring Time for Ladle Casting Machine using Aluminium Alloy

Pouring Temperature (°C)	Time (sec)			Total Time (sec)
	Lifting & Movement	Lowering & Movement	Pouring	
726	26.16	7.72	17.85	51.73
730	30.05	7.54	19.37	56.96
716	26.91	7.80	17.03	51.74
Average	27.71	7.69	18.08	53.48

Table 4.4: Result of Pouring Time for Hand-shank Ladle using Aluminium Alloy

Pouring Temperature (°C)	Time (sec)			Total Time (sec)
	Lifting & Movement	Lowering & Movement	Pouring	
729	29.63	34.89	20.13	84.65
725	28.25	33.98	17.40	79.63
718	29.31	34.08	17.72	83.11
Average	29.06	34.32	18.42	81.80

4.1.2 Determination of the Speed of Pouring

The result of the calculations for speed of pouring the molten metal into the mould until it was filled for both the ladle machine and manual hand-shank ladle are calculated using equation 3.22. The height from crucible to sprue basin (H) was maintained in both at 8 cm while the time taken (T_p) for pouring the molten Aluminium alloy metal into the mould until it fills the mould are 18.08 sec and 18.42 sec (from Tables 4.3 and 4.4) respectively.

The speed of pouring for the ladle machine was,

$$V_{LM} = \frac{H}{T_p} = \frac{8}{18.08} = 0.44 \text{ cm/s}$$

The speed of pouring when using the hand-shank ladle,

$$V_{HL} = \frac{H}{T_p} = \frac{8}{18.42} = 0.43 \text{ cm/s}$$

4.1.3 Non-destructive Test

4.1.3.1 Visual Inspection of the Casts

This test was carried out by observing the two castings using the physical eye inspection to detect the casting defects especially misrun and cold shut. From the visual inspection, the following were observed.

- For the cast using the pouring ladle, there were very few or no sand blows on the cope side of the water jacket (Plate 4.1 and 4.2) and crank lever (Plate 4.3 and 4.4) cast while some little sand blows were seen on the bearing cap (plate 4.5 and 4.6). But on the drag side, some sand blows were seen on the water jacket, crank lever and bearing cap cast. Although the sand blows in the cast of pouring ladle machine are few compared to those of the hand-shank ladle. Also on the crank lever cast, joint flash defect was observed.
- While for the cast using the hand-shank ladle, there were some noticeable sand blows on the cope side of the water jacket (Plate 4.7 and 4.8), crank lever (Plate 4.7 and 4.10) and bearing cap (Plate 4.11 and 4.12). There was splash seen on the left side of the crank lever. Joint flash defect was observed on crank lever and bearing cap casts.



Plate 4.1: Cope side of the water jacket Plate 4.2: Drag side of the water jacket cast using ladle machine pouring cast using ladle machine pouring



Plate 4.3: Front side of the crank lever cast using ladle machine pouring



Plate 4.4: Rear side of the crank lever cast using ladle machine pouring



Plate 4.5: Cope side of the bearing cap cast using ladle machine pouring



Sand blow

Plate 4.6: Drag side of the bearing cap cast using ladle machine pouring



Plate 4.7: Cope side of the water jacket cast using hand-shank ladle pouring



Plate 4.8: Drag side of the water jacket cast using hand-shank ladle pouring

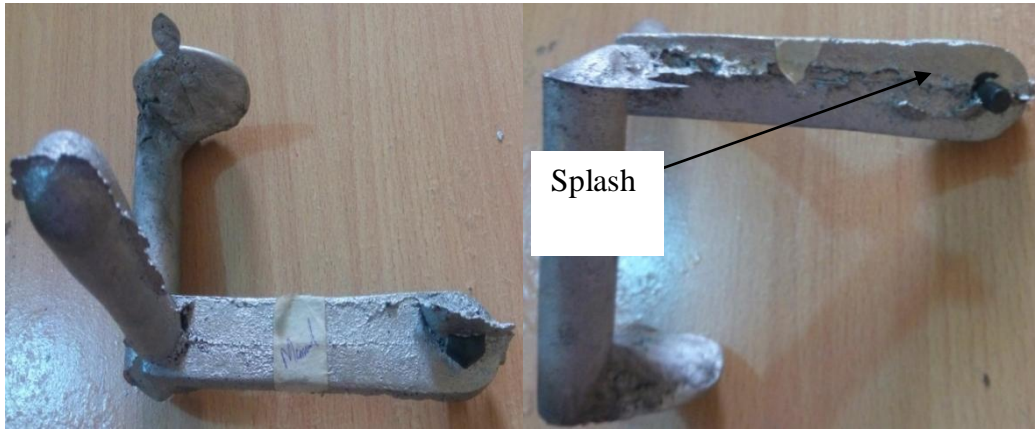


Plate 4.9: Front side of the crank lever
 Plate 4.10: Rear side of the crank lever
 cast using hand-shank ladle pouring cast using hand-shank ladle pouring



Plate 4.11: Cope side of the bearing cap
 Plate 4.12: Drag side of the bearing cap
 cast using hand-shank ladle pouring cast using hand-shank ladle pouring

4.1.3.2 Metallography examination of the cast

The result of the metallography examination for the cast samples produced from both pouring ladle and hand-shank ladle shows clearly the spherical dimples characteristics of grain type (Plate 4.13a and b). In these microstructures, the hypoeutectic structure consists of primary α solid solution of silicon in aluminium α (white patches) in a matrix of eutectic $\alpha + \text{Si}$ (dark patches).


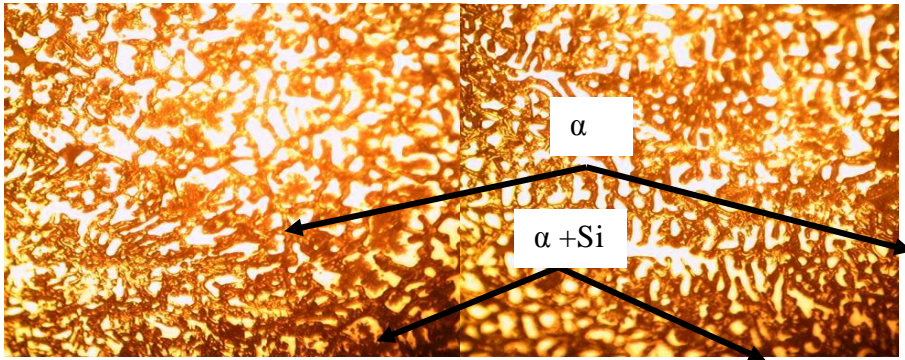


Plate 4.13a: Micrograph test for sample using pouring ladle machine (X 100)


Plate 4.13b: Micrograph for sample using hand-shank ladle(X 100)

4.1.3.3 X-Ray Fluorescence (XRF) test of the cast


The result of the XRF at different energy levels reveals the chemical compositions of the various samples. Plates 4.14 and 4.15 shows the spectra of the cast sample of pouring ladle machine and that of the hand-shank ladle. Also, Table 1 (in Appendix C) shows the chemical composition of both samples using.

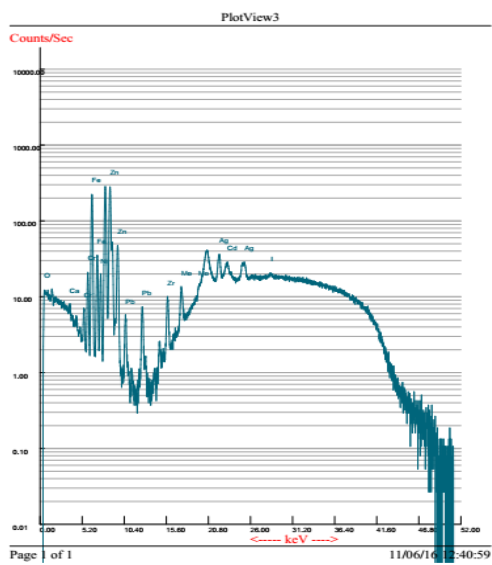


(a)

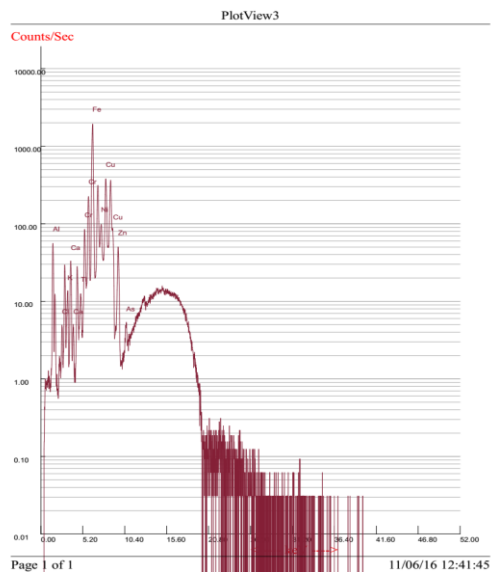

(b)

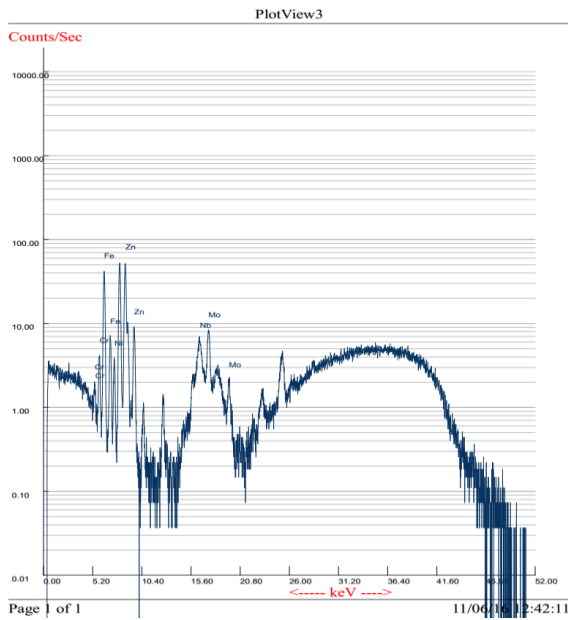


(c)

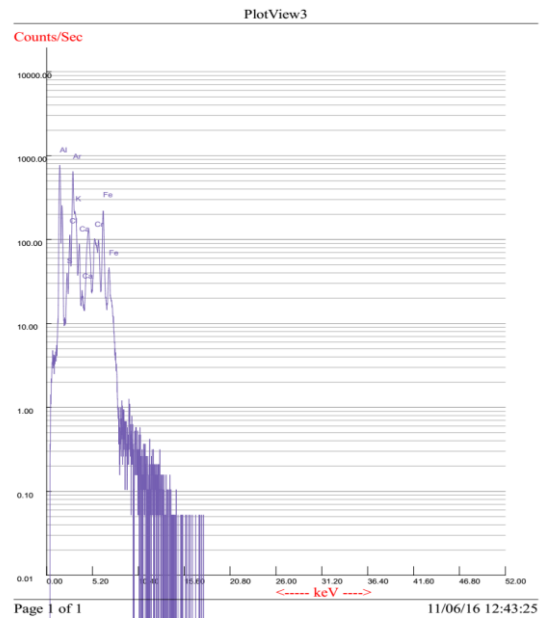


(d)


Plate 4.14: Spectra for cast sample from machine ladle at different energy levels

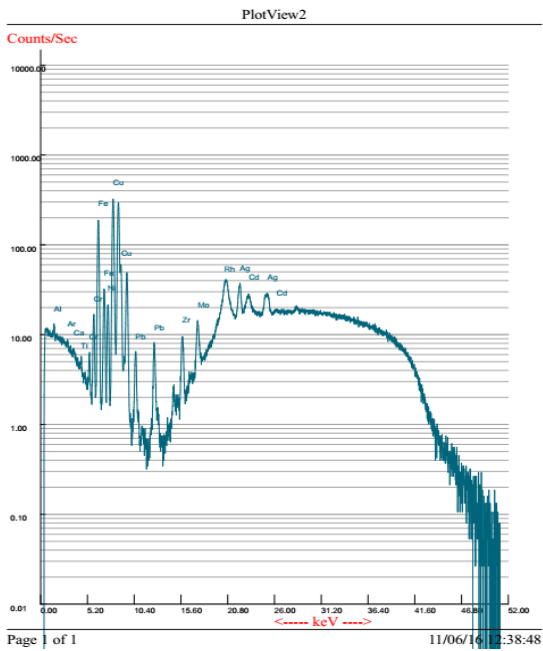


(a)

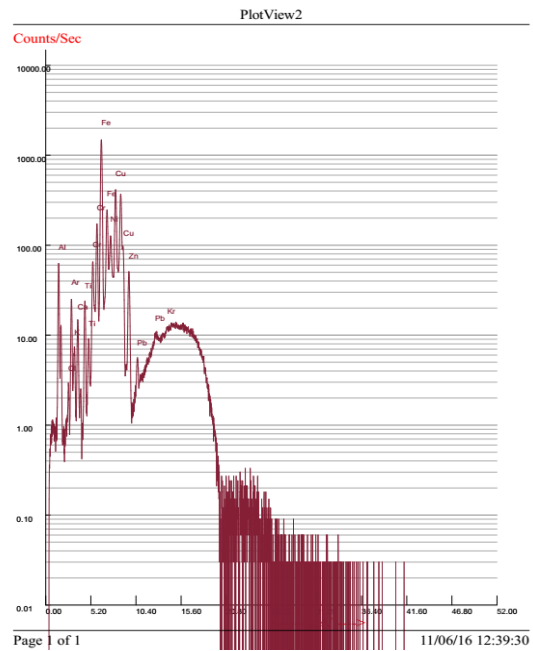

(b)

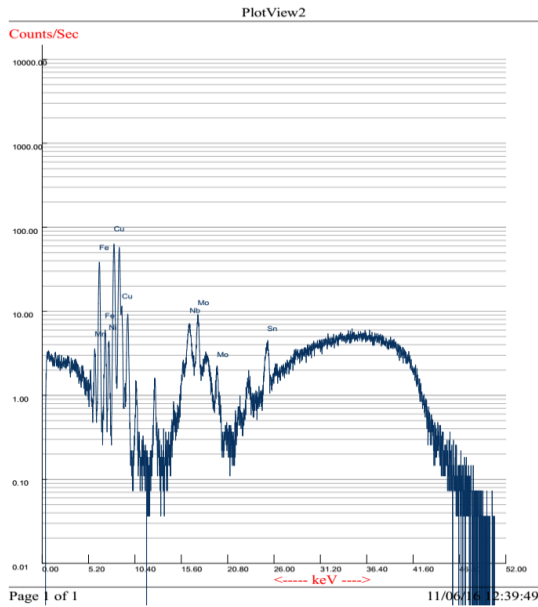

(c)

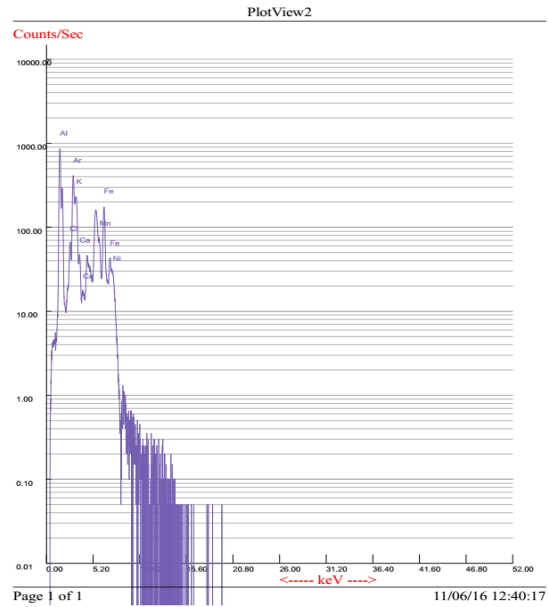

(d)

Plate 4.15: Spectra for cast sample from hand-shank ladle at different energy levels

4.2 Discussion of Results

4.2.1 Result of Performance Evaluation of the Pouring Ladle

4.2.1.1 Result of Performance Evaluation Using Water

From Tables 4.1 and 4.2, the total time spent from lifting the crucible from the furnace to filling the “Jerry can” using both the ladle casting machine and hand-shank ladle were 88.78 sec, 120.12 sec respectively. It was discovered that when using the ladle casting machine, time spent on lifting of the crucible from the furnace to pouring to fill the “Jerry can” was shorter by 31.34 sec. This was because there was too much time used in lowering the crucible, removing the tong from gripping the crucible and then lifting it using the hand-shank ladle to the location of the mould for pouring of the molten metal. While when using the ladle casting machine, it was discovered that little time was spent in lowering and movement of the crucible for pouring. There will be no need of dropping the crucible then removing the tong from gripping the crucible. Therefore, there was a time saving of about 26.1%. Figure 4.1 shows the result of the average time of pouring water using both ladle casting machine and hand-shank ladle at the various activities.

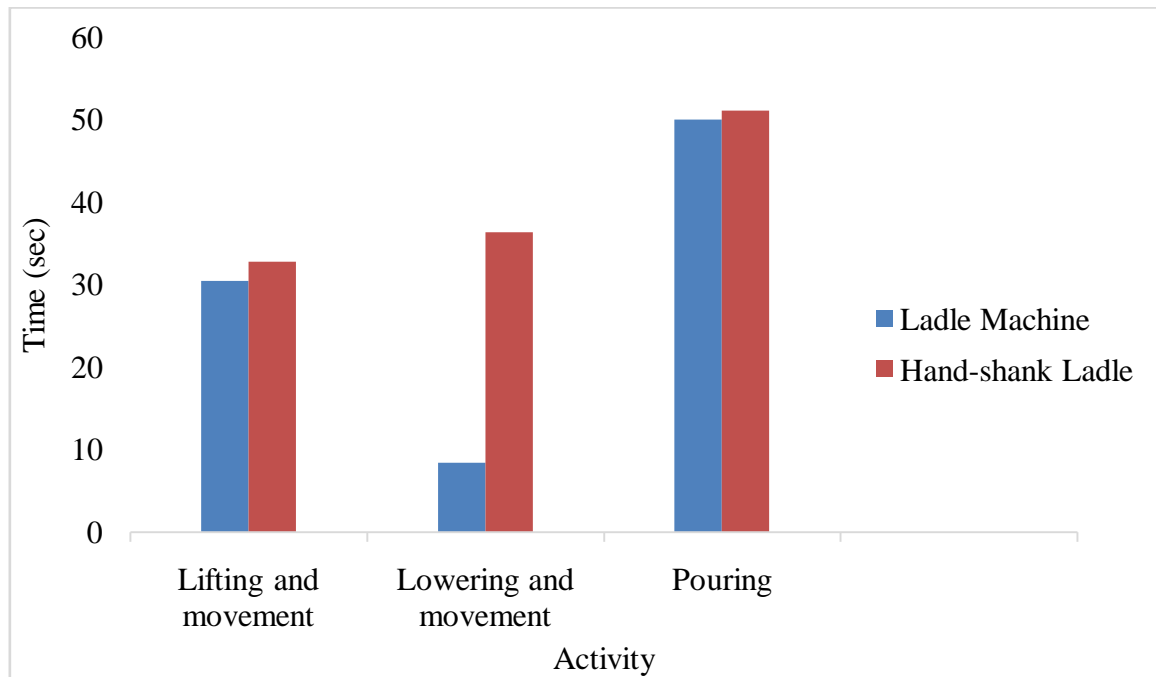


Figure 4.1: Average pouring time for the ladle machine and hand-shank ladle using water

4.2.1.2 Result of Performance Evaluation Using Aluminium Alloy Molten Metal

Similarly, from Tables 4.3 and 4.4, the total time spent from lifting the crucible from the furnace to filling the mould using both the ladle casting pouring ladle and hand-shank ladle were 53.48 sec, 81.80 sec respectively. The time difference in lifting of the crucible from the furnace to pouring to fill the mould can was shorter by 28.32 sec. The time saving was about 34.62 %. Figure 4.2 shows the result of the average time of pouring molten Aluminium alloy metal using both ladle casting machine and hand-shank ladle at the various activities.

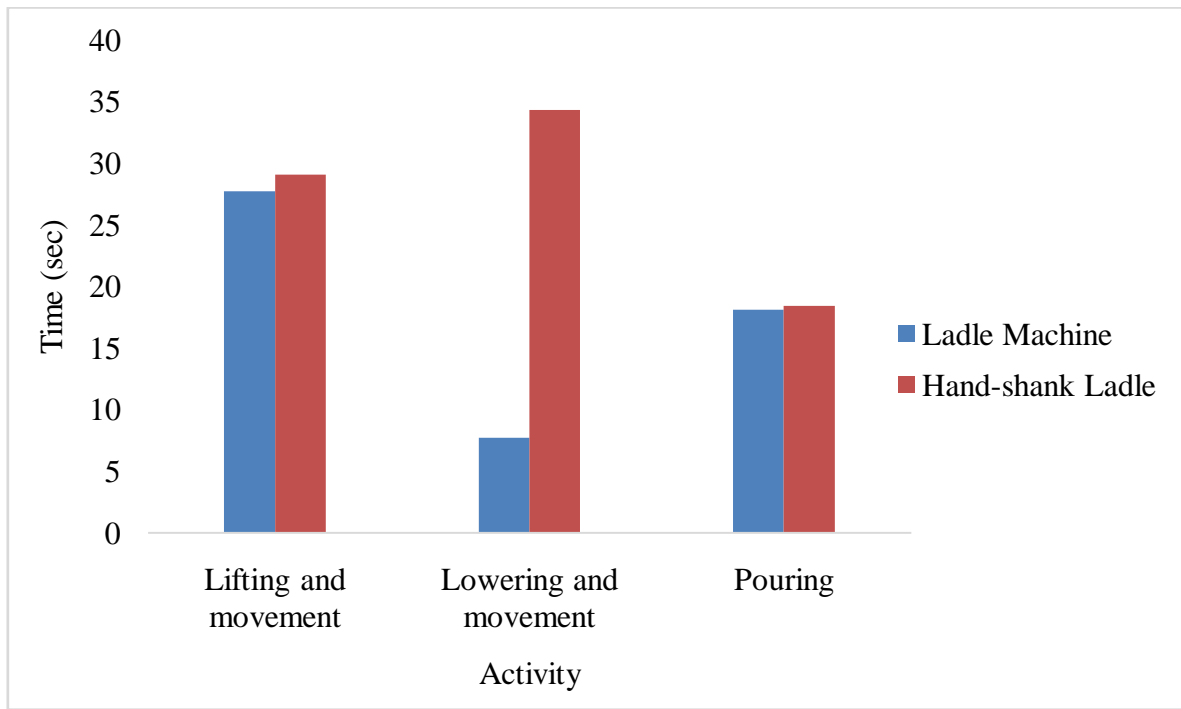


Figure 4.2: Average pouring time for ladle machine and hand-shankladle using Aluminium alloy molten metal

4.2.1.3 Result of the Speed of Pouring

The results of the pouring speed when using the ladle casting machine and hand-shank ladle from Table 4.3, Table 4.4 and Equation 3.22 were 0.44 cm/s and 0.43 cm/s respectively. The pouring speed when using the ladle casting machine was faster than that of the hand-shank ladle by 0.01cm/sec (2.33 % speed increase). This was because the time taken to fill the mould when using the ladle casting machine was less as compared to when using the hand-shank ladle. When using the gearing system, the pouring was at a relatively consistent flow unlike the manual method where the pouring was inconsistent as a result of different persons (operators) handling the hand-shank ladle.

4.2.2 Non-destructive Test

4.2.2.1 Visual Inspection of the Casts:

There was no any misrun or cold shut in both machine and manual casts. This was because the pouring temperature was adequate enough not to allow for sudden solidification as the

molten metal enters the mould. Also, the pouring speed was not too slow to allow for the solidification of the molten metal as it enters the mould.

The physical defect that was observed from the casts was sand blows especially on the drag side of the casts which are numerous in the casts of manual hand-shankladle as compared to the casts of ladle machine. The defects may be as a result of gases entrapped in the casts as well as mould sand particles which were entrapped on the surface of the casts. Gases are entrapped in casting when there is no proper venting in the mould, while mould sand are entrapped or attached to the surface of the casting if loosed i.e. sand not properly bounded together.

4.2.2.2 Metallography Test:

The micrograph of both samples show visible well defined coarse grain boundaries. This could be due to the even distribution of the constituents as cooling takes place since no too much time was taken to pour the liquid metal into the mould. In these microstructures, the samples were of hypoeutectic structure consisting of primary α solid solution of silicon in aluminium α (white patches) in a matrix of eutectic $\alpha + \text{Si}$ (dark patches).

According to Raji and Khan (2006), the results of metallographic studies of the cast samples showed that in all cases, the microstructure of the cast samples were of hypoeutectic structure consisting of primary α solid solution of silicon in aluminium (α) in a matrix of eutectic ($\alpha + \text{Si}$). However, the grain sizes differed for various castings. The results of micro-examination revealed that the dendrites of aluminium in squeeze castings are fine with the fineness increasing with increase in squeeze pressure for all pouring temperatures.

4.2.2.3 X-Ray Fluorescence (XRF) test of the cast:

The result of the XRF tests shows the presence of the various elements detected in the alloy with their percentages at different energy level. It can be observed the percentage of Silicon detected is high; therefore, the alloy is Aluminium-silicon alloy.

CHAPTER FIVE

CONCLUSION AND RECOMMENDATIONS

5.1 Conclusion

To obtain a cast with little or no cast defects such as cold shut and misruns resulting from pouring of liquid/molten metal from a crucible into a prepared mould, there is a need to design and fabricate a manual ladle machine for casting.

From this research, the following conclusion could be drawn:

1. A ladle casting machine of 50 kg charge capacity of molten Aluminium alloy was successfully designed and constructed. The pouring ladle was designed such that it would be used to pick the crucible from the furnace and pour the molten Aluminium alloy directly without delay. The delay in time spent to drop the crucible, remove the tong from gripping the crucible then picking it up by using the hand-shank ladle is eliminated.
2. The construction/fabrication of the components/parts of the ladle machine was successfully carried out. The various component parts were assembled together to form the pouring ladle. The ladle was used to cast molten Aluminium alloy into a prepared sand mould.
3. The pouring ladle was used for casting as well as the hand-shank ladle. The results of the castings were compared. From the results obtained, the pouring ladle recorded a few pouring time in the casting activity using both water and molten Aluminium alloy. The time difference is not too much except in the activity of lowering and movement were in the case of hand-shank ladle, too much time (34.32 sec) was spent while less time (7.69 sec) spent when using the pouring ladle to cast the Aluminium alloy. Also, the pouring speed when using the ladle casting machine was faster (2.33 % speed increase) than that of the hand-shank ladle by 0.01 cm/sec. This was because

the time taken to fill the mould when using the ladle casting machine was less as compared to when using the hand-shank ladle.

4. The results of the non-destructive tests showed no casting defect like cold shut or misrun. This was because the pouring temperature was adequate enough with no delay in the pouring from both the pouring ladle and hand-shank ladle which may result into sudden solidification inside the mould without completely filling the mould cavity. The micrograph of both samples show visible well defined coarse grains. This could be due to the even distribution of the constituents as cooling takes place since no too much time was taken to pour the liquid metal into the mould. The result of the XRF tests shows the presence of the various elements detected in the alloy with their percentages at different energy level and showed that the percentage of Silicon detected was high.

5.2 Recommendations

1. Further research, design and fabrication could be carried out for casting of cast iron metal since this design was for 50 kg molten Aluminium alloy only.
2. Design and construction/fabrication could be carried out to automate similar design for 100 kg and above charge capacity by using electric motor with remote control.

5.3 Contribution to knowledge

The following are the contributions to knowledge

1. Percentage time saving (about 35.28%) in the pouring process of casting molten Aluminium alloy since lifting and pouring of hot crucible containing molten metal can be done directly without delay.
2. Reduction of labour and cost since one person (operator) can handle the work of two or more persons (operators) and no need of electricity or electric motor. When using the pouring

ladle to cast, only one operator is needed unlike when using the hand-shank ladle where two or more operators are needed. This reduces the labour cost. Also, if the pouring ladle were to be driven by an electric motor, the cost of using electricity to drive electric motor will increase cost of production. But this pouring ladle doesn't need electric motor because it is operated manually by using crank lever arms.

REFERENCES

- Baker, J. (1997). Five Thousand Years of Investment Castings. *BICTA Bulletin*, No.26, p.6-8.
- Choudhari, C. M., Narkhede, B. E. and Mahajan, S. K. (2014). *Methoding and Simulation of LM 6 Sand Casting for Defect Minimization with its Experimental Validation*. 12th global congress on manufacturing and management (GCMM), 2014. Institute of Technology, Navi Mumbai, 400703 India. *Procedia Engineering* 97(2014) 1145–1154. Retrieved from www.sciencedirect.com/science/article/pii/S1877705814034614
- Ciriello, V.M. (2005). The Effects of Box Size, Vertical Distance, and Height on Lowering Tasks for Female Industrial Workers. *International Journal of Industrial Ergonomics* 35, 857–863.
- Dempsey, P.G., Hashemi, L. (1999). *Analysis of worker's compensation claims associated with manual materials handling*. *Ergonomics* 42, 183–195.
- Derya D. (2005). Determination of Metal Quality of Aluminium and Its Alloys. School of Metallurgy and Materials. University of Birmingham.
- Kalpakjian, S. (1995). *Manufacturing Engineering and Technology*. 3rd Ed. Addison Wesley.
- Khurmi, R.S. and Gupta, J. K. (2005). *Machine Design*. Eurasia Publishing House (PVT) Ltd. Ram Nagar, New Delhi – 110055.
- Konz, S. (1995). *Manual Material Handling*. In: Proceedings of the Annual Conference— Human Factors Association of Canada, vol. 27, pp. 13–26.
- Krzysztof, G., Marcin, W. and Kamil, S. (2013). *The Effect of the Method of Pouring Liquid Metal into Mould on Misrun Formation in the Castings Made with Lost-Wax Casting Technology*. *Archives of Mechanical Technology and Automation* vol. 33 no, 4, 2013.
- Ndaliman, M.B. and Pius, A. (2007). *Behavior of Aluminum Alloy Casting under Different Pouring Temperatures and Speeds*. *Leonardo Electronic Journal of Practices and Technologies*. ISSN 1583-1078. pp. 71-80.

- Niraj, M. (2013). *Review of Ladle Furnace. Proceedings of 7th ICEECSME-2013. BMIT, Maharashtra, India. ISBN:978-93-82702-43-6. Retrieved from www.iraj.in/up_proc/pdf/32-138601653665-70.pdf.*
- Peter, R.B. (2001). *Foundry Technology. 2nd Ed. Butterworth-Heinemann, Lancre House, Jordan Hill, Oxford OX2 8DP, 225 Wildwood Avenue, Woburn, MA 01801-2041, A division of Reed Educational and professional Publishing Ltd. ISBN 0750645679*
- Raji, A. and Khan, R.H. (2006). *Effects of Pouring Temperature and Squeeze Pressure on Al-8%Si Alloy Squeeze Cast Parts. Department of Mechanical Engineering, Federal University of Technology Yola, Adamawa State, Nigeria .AU J.T. 9(4): 229-237 (Apr. 2006)*
- Rajput, R. K. (2013). *Strength of Materials. (Mechanics os Solid SI unit). S. Chand and Company ltd. Ram Nagar, New Delhi – 110055.*
- Richard, W.H., Carl, R.L. (Jr) and Philip, C.R. (1967). *Principles of Metal Casting. 2nd Ed. McGraw-Hill Book Company.*
- Robinson, E. (2012). *Effect of Sand Casting Process Parameters on Mechanical Properties of Aluminium Alloy. International Journal of Metallurgical and Materials Science and Engineering (IJMMSE). ISSN 2278-2516. Vol.2, Issue 3 September 2012 pp32-41.*
- Sharma, P.C. (2001). *A Textbook of Production Technology (manufacturing Processes). 3rd Ed. S. Chad and Company Ltd. Ram Nagar, New Delhi-110055. ISBN: 8121911141*
- Yoshiyuki, N. and Kazuhiko, T. (2007). *Modeling and Feedforward Flow Rate Control of AutomaticPouring System with Real Ladle. Toyohashi, Aichi 441-8580, Japan. Journal of Robotics and Mechatronics Vol.19 No.2.*

APPENDIX A

DRAWINGS OF THE MACHINE AND MACHINE COMPONENTS (ENCLOSED)

1. Drawing 1: Casting pouring ladle
2. Drawing 2: Casting Pouring Ladle
3. drawing 3: Machine Frame
4. drawing 4: Components of Rail Mechanism
5. drawing 5: Components of Lifting/Lowering System
6. drawing 6: Components of Tilting System
7. drawing 7: Components of Gripping System

APPENDIX B

FABRICATION PROCESSES AND PERFORMANCE EVALUATION OF THE LADLE MACHINE



Plate I: Turning of shafts using lathe machine

Plate II: Drilling of plate using drilling machine



Plate III: Welding of the rail track

Plate IV: Forging of gripping tong



Plate V: Using the pouring ladle for performance evaluation using water

Plate VI: Using the hand-shank ladle for performance evaluation using water

APPENDIX C

RESULT OF XRF TEST FROM CENTRE FOR MINERALS RESEARCH AND
DEVELOPMENT, KADUNA POLYTECHNIC

Kaduna Polytechnic

Centre for Minerals Research & Development

SCIENCE AND TECHNOLOGY EDUCATION POST-BASIC (STEP-B) PROJECT (World Bank Assisted)

Rector: Dr. M.B. Ibrahim

BSc, MSc, PhD, FCSN

Project Manager: Engr. Dr. S.N. Mumah

B.Eng, MSc, PhD(Chem.Eng), FNSChE, MNSE, R.Eng

Tel: +234(0)8037619719 **e-mail:** stepbkadpoly@yahoo.co.uk



STEP-B Project Office
Kaduna Polytechnic,
P.M.B. 2021, Tudun Wada,
Kaduna, Nigeria

19th of November, 2016.

Stephen Emmanuel

Department of Mechanical Engineering,

Ahmadu Bello University, Zaria.

Dear Client:

Please find attached the result of your XRF analysis shown in Table 1.

We are grateful for your patronage.

Engr. Dr. H. F. Akande (08033686645)
For Centre Manager

Table 1: Elemental Composition of Machine and Manual Cast Samples using X-Ray Fluorescence (XRF)

Element	Machine Cast Sample	Manual Cast Sample
Mg	1.272	2.129
Al	81.622	81.514
Bal	<LOD	<LOD
Si	10.987	11.502
P	<LOD	0.165
S	0.311	0.081
Cl	<LOD	<LOD
K	0.094	<LOD
Ca	0.276	0.118
Ti	0.071	0.072
V	<LOD	<LOD
Cr	0.094	0.056
Mn	0.346	0.252
Fe	2.597	1.929
Co	<LOD	<LOD
Ni	0.061	0.067
Cu	1.27	1.236
Zn	0.917	0.811
As	<LOD	<LOD
Se	<LOD	<LOD
Rb	<LOD	<LOD
Sr	<LOD	<LOD
Zr	0.004	0.004
Nb	<LOD	<LOD
Mo	0.004	0.004
Pd	<LOD	<LOD
Ag	<LOD	<LOD
Cd	0.003	0.002
Sn	0.024	0.02
Sb	<LOD	<LOD
Ba	0.022	0.016
W	<LOD	<LOD
Au	<LOD	<LOD
Pb	0.021	0.019
Bi	<LOD	<LOD
Total	99.996	99.997